

## Stress Overshoots in Simple Yield Stress Fluids

**Citation for published version (APA):**

Benzi, R., Divoux, T., Barentin, C., Manneville, S., Sbragaglia, M., & Toschi, F. (2021). Stress Overshoots in Simple Yield Stress Fluids. *Physical Review Letters*, 127(14), Article 148003.  
<https://doi.org/10.1103/PhysRevLett.127.148003>

**DOI:**

[10.1103/PhysRevLett.127.148003](https://doi.org/10.1103/PhysRevLett.127.148003)

**Document status and date:**

Published: 01/10/2021

**Document Version:**

Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

**Please check the document version of this publication:**

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

**General rights**

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

[www.tue.nl/taverne](http://www.tue.nl/taverne)

**Take down policy**

If you believe that this document breaches copyright please contact us at:

[openaccess@tue.nl](mailto:openaccess@tue.nl)

providing details and we will investigate your claim.

## Stress Overshoots in Simple Yield Stress Fluids

Roberto Benzi,<sup>1</sup> Thibaut Divoux<sup>1,2</sup>, Catherine Barentin<sup>1,3</sup>, Sébastien Manneville,<sup>2</sup>  
Mauro Sbragaglia,<sup>1</sup> and Federico Toschi<sup>4</sup>

<sup>1</sup>*Dipartimento di Fisica, Università di Roma “Tor Vergata” and INFN, Via della Ricerca Scientifica, I-00133 Roma, Italy*

<sup>2</sup>*Univ Lyon, Ens de Lyon, Univ Claude Bernard, CNRS, Laboratoire de Physique, F-69342 Lyon, France*

<sup>3</sup>*Université de Lyon, Université Claude Bernard Lyon 1, CNRS, Institut Lumière Matière, F-69622 Villeurbanne, France*

<sup>4</sup>*Department of Applied Physics, Eindhoven University of Technology, P.O. Box 513,  
5600 MB Eindhoven, Netherlands and CNR-IAC, Rome, Italy*



(Received 31 March 2021; revised 25 June 2021; accepted 1 September 2021; published 27 September 2021)

Soft glassy materials such as mayonnaise, wet clays, or dense microgels display a solid-to-liquid transition under external shear. Such a shear-induced transition is often associated with a nonmonotonic stress response in the form of a stress maximum referred to as “stress overshoot.” This ubiquitous phenomenon is characterized by the coordinates of the maximum in terms of stress  $\sigma_M$  and strain  $\gamma_M$  that both increase as weak power laws of the applied shear rate. Here we rationalize such power-law scalings using a continuum model that predicts two different regimes in the limit of low and high applied shear rates. The corresponding exponents are directly linked to the steady-state rheology and are both associated with the nucleation and growth dynamics of a fluidized region. Our work offers a consistent framework for predicting the transient response of soft glassy materials upon startup of shear from the local flow behavior to the global rheological observables.

DOI: [10.1103/PhysRevLett.127.148003](https://doi.org/10.1103/PhysRevLett.127.148003)

**Introduction.**—From dense suspensions and gels to metallic alloys and composites, numerous materials display a nonmonotonic stress response under external shear. For a given applied shear rate  $\dot{\gamma}$ , the stress increases up to a maximum  $\sigma_M$  reached at a strain  $\gamma_M$  before decreasing towards its steady-state value, while the sample yields (see Fig. 1). This sequence, also referred to as the “stress overshoot,” is a complex process to model as it depends on the applied shear rate as well as the details of the sample microstructure through the sample age, its thermal and shear history, etc. [1–6].

Soft glassy materials (SGMs) encompass soft amorphous systems such as gels and glasses. These materials are characterized by a yield stress  $\sigma_y$  below which the sample responds as a solid, and above which it flows like a liquid [4]. Under external shear, most SGMs display a stress overshoot, which results from the rearrangement of the sample microstructure. The stress peak is correlated to the maximum structural anisotropy [8,9], while the subsequent stress relaxation is dominated by nonaffine displacements, and associated with either cage breaking and superdiffusive motion of particles in the case of glasses [9–11], or strand failure in the case of gels [12–14]. Concomitantly to the stress relaxation, the sample may either flow homogeneously or show the formation of transient or steady-state shear bands, or even fracture [15–19].

Despite such complexity, the amplitude  $\sigma_M$  of the stress overshoot consistently increases as a power law of  $\dot{\gamma}$ , with an exponent that varies from 0.1 to 0.5 as reported in

experiments on gels and repulsive glasses [7,19–22]. Stress overshoots are well reproduced by various theoretical approaches such as Brownian or molecular dynamics simulations, micromechanical modeling, and mode coupling theory, which have provided valuable insights on the microscopic scenario associated with the overshoot [19,23–26]. However, the functional form  $\sigma_M(\dot{\gamma})$  inferred from computations is most often either logarithmic [27–30] in contradiction with experimental results, or a power law with an exponent 0.5 [12,13,31], which does not reflect the broad range of exponents reported in the literature. A noticeable exception is the seminal version of the fluidity model, which yields a power-law scaling, with exponents lower than 0.5 [20]. However, to date, there is no consistent theoretical framework offering a rationale for the multiplicity of power-law exponents reported for stress overshoots in SGMs.

In this Letter, we tackle the case of “simple” yield stress fluids (YSFs), a subclass of SGMs whose steady-state flow is homogeneous and described by a Herschel-Bulkley rheology [4]. We use a model first introduced in Ref. [32] based on a fluidity parameter, and successfully extended to capture the spatially resolved yielding scenario of SGMs [33,34], to rationalize the effect of shear on the coordinates  $(\gamma_M, \sigma_M)$  of the stress overshoot. We show that the relevant variable to quantify the magnitude of the stress overshoot is  $\sigma_M/\sigma_y - 1$ , and that this normalized parameter displays two asymptotic power-law regimes as a function of the applied shear rate, namely, a diffusive regime for low

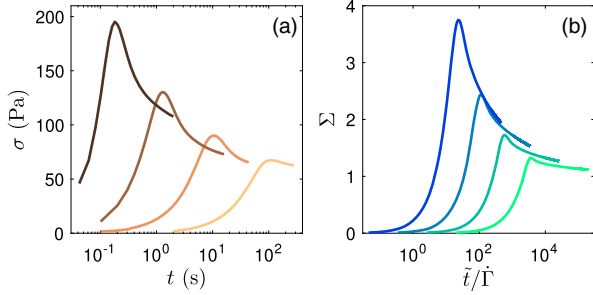


FIG. 1. Phenomenology of the stress overshoot during startup of shear. Stress responses (a)  $\sigma$  as a function of time  $t$  in experiments performed on a 1% wt. Carbopol microgel (adapted from Fig. 3 in Ref. [7]) under imposed shear rates  $\dot{\gamma} = 10, 1, 0.1$ , and  $0.01 \text{ s}^{-1}$  from left to right and (b) the present fluidity model for  $\dot{\Gamma} = 0.22, 2.9 \times 10^{-2}, 3.8 \times 10^{-3}$ , and  $5.1 \times 10^{-4}$  with a fixed value of  $\tau = 1$  (see text for details).

shear rates and an asymptotic scaling at large shear rates. In both cases, the value of the exponent is set by the power-law constitutive behavior in steady-state flow. Finally, our approach allows us to account not only for the shear dependence of the stress overshoots but also for the local flow behavior upon startup of shear.

*Fluidity model.*—We consider a simple YSF whose steady-state rheology follows the Herschel-Bulkley (HB) model, which reads  $\Sigma = 1 + \dot{\Gamma}^n$  in dimensionless units, where  $\Sigma = \sigma/\sigma_y$  is the shear stress normalized by the yield stress, and  $\dot{\Gamma} = \dot{\gamma}/(\sigma_y/A)^{1/n}$  is the shear rate normalized by the natural frequency for the HB model,  $\sigma = \sigma_y + A\dot{\gamma}^n$ , with  $n$  the HB exponent and  $A$  the consistency index. The fluid is sheared between two walls, separated by a distance  $L$  and its dynamics is encoded in the local dimensionless fluidity  $f(y)$ , where  $y$  is the spatial coordinate along the velocity gradient direction. As originally introduced in Ref. [32], the fluidity is a dynamical coarse-graining parameter related to the rate of plastic events. More intuitively, one can consider the fluidity as the inverse of the viscosity. We also define the rescaled time  $\tilde{t} \equiv \dot{\gamma}t$ , which corresponds to the physical strain. As discussed in Ref. [34], the fluid rheological response is well described by the following equation for the fluidity:

$$\frac{\partial f}{\partial \tilde{t}} = f[\xi^2 \Delta f + mf - f^{3/2}], \quad (1)$$

where  $\xi$  is the so-called cooperativity length and relates to the extension of the region that is impacted by a neighboring plastic rearrangement [32,35–38], and  $m = m(\Sigma)$  with  $m^2 = (\Sigma - 1)^{1/n}/\Sigma$  for  $\Sigma \geq 1$  and  $m = 0$  for  $\Sigma < 1$ . The latter parameter  $m$  essentially conveys the information about the underlying steady-state HB rheology, as  $f = m^2$  corresponds to the stationary homogeneous solution of Eq. (1). Moreover, we assume a simple plane shear flow and that  $\Sigma$  is spatially homogeneous and only depends on  $t$ .

To model the response to an imposed shear rate  $\dot{\Gamma}$ , Eq. (1) is coupled to the following evolution equation for the stress based on a Maxwell model:

$$\frac{d\Sigma}{d\tilde{t}} = \frac{G_0}{\sigma_y} \left( 1 - \frac{\langle f \rangle \Sigma}{\dot{\Gamma}} \right), \quad (2)$$

where  $G_0$  is the elastic modulus, and  $\langle f \rangle$  is the spatial average of the fluidity, which is a function of time. We have shown that this approach successfully captures the long-time evolution of SGMs towards steady state [33,34]. Here we explore the short-time response of this model during shear startup. As a generic case, we solve Eqs. (1) and (2) with  $n = 1/2$ , for fixed values of  $\dot{\Gamma}$  ranging between  $10^{-4}$  and  $10^2$  with  $\xi/L = 0.04$  and assuming  $f(y, 0) = 10^{-4} \ll 1$  for the initial solidlike state and  $f(0, \tilde{t}) = m^2[\Sigma(\tilde{t})]$  and  $\partial_y f(L, \tilde{t}) = 0$  for boundary conditions at the two different walls. In this framework, we explore the behavior of a simple YSF with respect to two parameters, i.e., the imposed shear rate  $\dot{\Gamma}$  and the dimensionless relaxation time  $\tau = \sigma_y/G_0$ .

*Theoretical scalings.*—As illustrated in Fig. 1(b) for four values of  $\dot{\Gamma}$ , the model predicts stress overshoots very similar to those reported in experiments, e.g., on Carbopol microgels [Fig. 1(a)]. More generally, extracting the stress maximum  $\Sigma_M(\dot{\Gamma})$  and the corresponding strain  $\Gamma_M(\dot{\Gamma}) = \tilde{t}_M$  for values of  $\tau$  spanning three orders of magnitude, we find that  $\Sigma_M$  grows faster with  $\dot{\Gamma}$  as  $\tau$  decreases, i.e., when the elastic modulus  $G_0$  increases relative to the yield stress  $\sigma_y$  [Fig. 2(a)]. As a central result of this Letter, we show that the entire dataset can be rescaled onto the master curve of Fig. 2(b), which is composed of two power-law asymptotic limits, namely  $(\Sigma_M - 1) \sim \dot{\Gamma}^{1/3}$  for  $\dot{\Gamma} \ll 1$ , and  $(\Sigma_M - 1) \sim \dot{\Gamma}^{4/17}$  for  $\dot{\Gamma} \gg 1$ . These two limits are justified analytically in detail in the companion paper [39] and can be understood qualitatively as the signature of two different dynamical regimes for the nucleation and growth of a shear band of size  $\ell_b(\tilde{t})$  at the moving wall. Indeed, upon shear startup, the initial fluidity remains negligible and the stress  $\Sigma(\tilde{t})$  grows roughly linearly up to  $\Sigma(\tilde{t}_M) = \Sigma_M$  where the lhs of Eq. (2) must be zero, yielding  $\dot{\Gamma} = \langle f \rangle(\tilde{t}_M)\Sigma_M$ . Since the fluidity  $\langle f \rangle$  is dominated by the fluidity in the shear band, we may approximate  $f$  with the value of  $m^2(\tilde{t})$  for any applied shear rate, yielding  $\langle f \rangle(\tilde{t}) \sim \ell_b(\tilde{t})m^2(\tilde{t})/L$ , with  $m^2(\tilde{t}) \sim \Sigma(\tilde{t}) \sim \Sigma(\tilde{t}) - 1$  under the assumption that  $\Sigma(\tilde{t}) \gg 1$ .

In the limit of large shear rates, the fluidity grows from the moving wall, triggering the formation of a fluidized front. Scaling arguments show that the characteristic length and time in the system are  $\xi/\sqrt{m}$  and  $m^{-3}$ , respectively [34,39]. Hence, the shear band is expected to move with a velocity  $d\ell_b/d\tilde{t} \sim m^3\xi/\sqrt{m} = \xi m^{5/2}(\tilde{t})$ . Using  $m(\tilde{t}) \sim [\Sigma(\tilde{t}) - 1]^{1/2}$  and integrating over time yields  $\ell_b(\tilde{t}) \sim \xi\tau[(\tilde{t} - \tilde{t}_1)/\tau]^{9/4}$ , where  $\tilde{t}_1$  is the time at which the stress

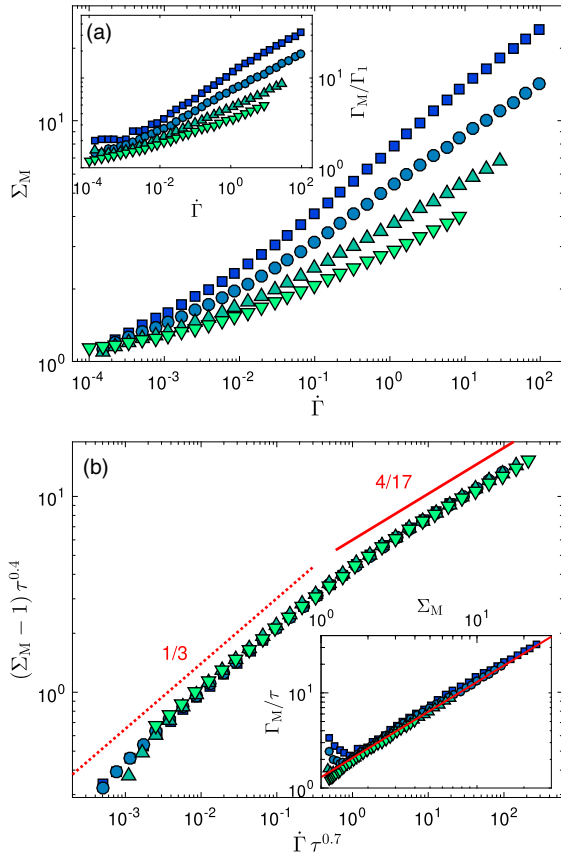


FIG. 2. Analysis of the stress overshoots predicted by the fluidity model for an HB exponent  $n = 1/2$ . (a) Stress maximum  $\Sigma_M$  vs shear rate  $\dot{\Gamma}$ . Inset: strain at maximum  $\Gamma_M$  normalized by the strain  $\Gamma_1$  that corresponds to  $\Sigma = 1$  and plotted against  $\dot{\Gamma}$ . Colored symbols refer to different values of  $\tau = 0.1$  (square), 1 (circle), 10 (triangle), and 100 (inverted triangle). (b) Rescaled stress maximum  $(\Sigma_M - 1)\tau^{0.4}$  vs  $\dot{\Gamma}\tau^{0.7}$ . Inset:  $\Gamma_M/\tau$  vs  $\Sigma_M$ . The red line is  $\Gamma_M/\tau = 1.3\Sigma_M$ .

equals the yield stress, i.e.,  $\Sigma(\tilde{t}_1) = 1$ . Finally, combining the expression of  $m(\tilde{t})$  and  $\ell_b(\tilde{t})$  at  $\tilde{t} = \tilde{t}_M$  and using  $\Sigma_M - 1 \sim \tilde{t}_M - \tilde{t}_1$  leads to an expression for  $\langle f \rangle(\tilde{t}_M)$  and to the following asymptotic scaling:

$$\Sigma_M - 1 \sim \left( \frac{\dot{\Gamma}}{\xi\tau} \right)^{4/17} \quad \text{for } \dot{\Gamma} \gg 1. \quad (3)$$

In the limit of low shear rates, the system reorganizes in the vicinity of the moving wall without any propagating front solution. Plastic activity rather occurs via diffusion effects, which are peculiar to the fluidity equation [Eq. (1)], so that the size of the shear band follows a diffusive growth  $\ell_b(\tilde{t}) \sim \xi m(\tilde{t})(\tilde{t} - \tilde{t}_1)^{1/2}$ . Following the same steps as in the high shear rate limit, we get

$$\Sigma_M - 1 \sim \left( \frac{\dot{\Gamma}}{\xi\tau^{1/2}} \right)^{1/3} \quad \text{for } \dot{\Gamma} \ll 1. \quad (4)$$

As shown in the inset of Fig. 2(b), the strain  $\Gamma_M$  is simply proportional to  $\Sigma_M$  so that the two asymptotic scalings also hold for  $\Gamma_M/\Gamma_1 - 1$ . Finally, combining Eqs. (3) and (4), we expect the transition between the two behaviors to occur at  $\dot{\Gamma}^* \sim \xi\tau^{-0.7}$  and  $\Sigma_M^* - 1 \sim \tau^{-0.4}$ . As shown in Fig. 2(b), the rescaled data  $(\Sigma_M - 1)\tau^{0.4}$  as function of  $\dot{\Gamma}\tau^{0.7}$  indeed nicely collapse onto the predicted master curve over the whole range of studied shear rates. As detailed in the companion paper [39], the above approach can be generalized to any value  $n$  of the HB exponent, leading to scalings with exponents  $\alpha = 4n/(9 - n)$  at large shear rates and  $\beta = 2n/3$  at small shear rates instead of  $4/17$  and  $1/3$  in Eqs. (3) and (4), respectively.

*Discussion.*—Let us now compare our theoretical findings against experimental data. We revisit the shear startup experiments of Ref. [7] performed on Carbopol microgels for concentrations ranging between 0.5% and 3% wt. in a parallel-plate geometry connected to a stress-controlled rheometer (see also the Supplemental Material [40] for details, which includes Refs. [7,38,41]). Such a simple YSF displays a stress overshoot upon shear startup [Fig. 1(a)]. As reported in Fig. 3(a), both the stress maximum  $\sigma_M$  and the corresponding strain  $\gamma_M$  increase weakly with the applied shear rate  $\dot{\gamma}$ . When considering  $\sigma_M/\sigma_y - 1$ , the experimental data for the stress can be further rescaled into a single master curve spanning more than two decades [Fig. 3(b)], which displays two asymptotic scalings in excellent agreement with the two exponents  $\alpha$  and  $\beta$  derived from the fluidity model for an arbitrary value of  $n$ . Moreover, when multiplied by the elastic modulus  $G_0$ , the strain  $\gamma_M$  collapses onto a single affine law of  $\sigma_M$  with the same prefactor as  $\Gamma_M/\tau$  in the theory [lower inset of Fig. 3(b)]. Therefore, our theoretical approach nicely captures the early stage response of this SGM to shear, as well as its subsequent fluidization [34].

Beyond the quantitative prediction of the locus of the stress maximum, our theoretical approach allows us to compute the local velocity profiles during shear startup. Figure 4 shows the velocity profiles at various times along the stress response of the material predicted for  $\dot{\Gamma} = 0.029$  and  $\tau = 1$ . The velocity profile is linear during the initial growth of the stress, which is indicative of affine displacement during the initial stage. Around the stress maximum, the fluidity at the moving wall becomes sufficiently large that the shear rate in the bulk decreases, leading to an elastic recoil after which the velocity profile flattens out. These results are in excellent agreement with the experimental observations on Carbopol microgels, in which the formation of a thin lubrication layer at the wall leads to a fast recoil followed by a total wall slip regime (lower inset in Fig. 4) [7].

Our theoretical approach provides the following rationale for the observed phenomenology. When shear is switched on, the fluidity at the wall and the thickness  $\ell_b$  of the shear band are small. At short times, and thus for

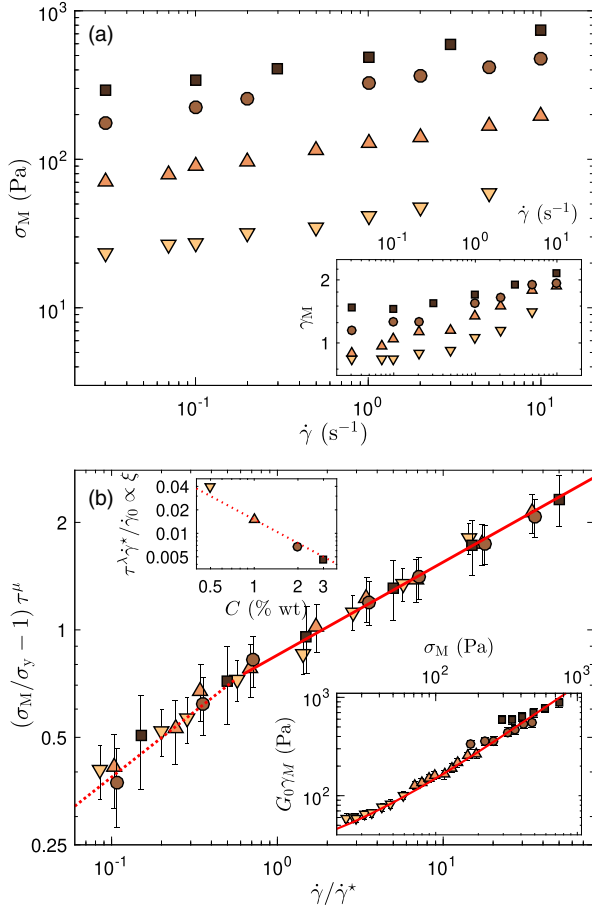


FIG. 3. Analysis of the stress overshoots recorded in experiments on Carbopol microgels with different concentrations  $C = 0.5\%$  (inverted triangle),  $1\%$  (triangle),  $2\%$  (circle), and  $3\%$  wt (square). (a) Stress maximum  $\sigma_M$  as a function of the applied shear rate  $\dot{\gamma}$ . Inset: corresponding strain  $\gamma_M$  vs  $\dot{\gamma}$ . Data from Ref. [7]. The experimental uncertainty on these raw data is smaller than the symbol size. (b) Rescaled stress maximum  $(\sigma_M/\sigma_y - 1)\tau^\mu$  vs  $\dot{\gamma}/\dot{\gamma}^*$ , where  $\tau = \sigma_y/G_0$ , with  $G_0$  the elastic modulus of the microgel. The red solid line is a power law with exponent  $\bar{\alpha} = \langle 4n/(9-n) \rangle = 0.27 \pm 0.01$  inferred from the fluidity model in the asymptotic regime and averaged over the various samples. The red dotted line shows the scaling predicted in the diffusive regime with exponent  $\bar{\beta} = \langle 2n/3 \rangle = 0.38 \pm 0.01$ . Lower inset:  $G_0\gamma_M$  vs  $\sigma_M$ . The red line is  $G_0\gamma_M = 1.3\sigma_M + 20$ . See Supplemental Material Table S1 [40] for the values of  $\sigma_y$ ,  $n$ , and  $G_0$  used in the rescaling. Error bars account for the experimental uncertainty on  $\sigma_y$  and  $G_0$ . Upper inset: rescaling factor  $\dot{\gamma}^*$  used for the shear rate as a function of  $C$  and normalized by  $\dot{\gamma}_0\tau^{-\lambda}$  with  $\dot{\gamma}_0 = (\sigma_y/A)^{1/n}$  so as to provide a quantity that is predicted by the theory to be proportional to the cooperativity length  $\xi$ . The red dotted line shows that this quantity scales roughly as  $1/C$ . The exponents  $\lambda$  and  $\mu$  are inferred from the HB exponent  $n$ , which depends weakly on the Carbopol concentration [42].

small  $\ell_b$ , the second term on the rhs of Eq. (2) does not play any significant role and the stress grows in time almost linearly. Around the stress maximum, the system enters a different dynamical regime where  $d\Sigma/d\tilde{t} \simeq 0$ ; i.e., the

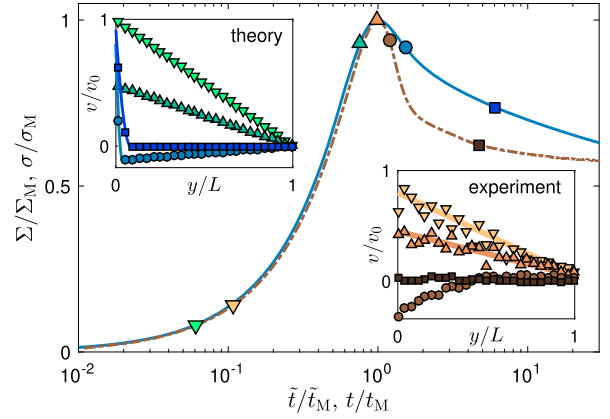


FIG. 4. Rescaled stress response  $\Sigma/\Sigma_M$  vs  $\tilde{t}/\tilde{t}_M$  from the fluidity model (blue solid line,  $\dot{\Gamma} = 0.029$  and  $\tau = 1$ ) and  $\sigma/\sigma_M$  vs  $t/t_M$  from experiments on a Carbopol microgel (brown dash-dotted line,  $\dot{\gamma} = 0.1 \text{ s}^{-1}$ ,  $C = 1\%$  wt, adapted from Fig. 4 in Ref. [7]).  $\tilde{t}_M$  ( $t_M$ ) corresponds to the strain (time resp.) at which the maximum stress  $\Sigma_M$  ( $\sigma_M$ ) is reached. Insets: velocity profiles  $v$  normalized by the velocity of the moving plate  $v_0$  as a function of the distance  $y$  to the moving plate normalized by the gap size  $L$  and taken at the various times indicated by the symbols in the main graph. Lines on the experimental profiles are guides for the eye.

instantaneous value of the stress is balanced by the effective shear rate within the shear band  $\dot{\Gamma}L/\ell_b$  [39]. The clear-cut separation between these two different dynamical behaviors allows us to provide a distinctive theoretical prediction for the scaling of the stress maximum as a function of the shear rate. Finally, note that the narrow fluidized band near the wall eventually grows into a transient shear band, whose dynamics and lifespan have been extensively discussed in Ref. [34].

To conclude, the present fluidity model encompassing nonlocal effects provides a comprehensive framework for describing the stress overshoot that goes along with the startup of shear in simple YSFs. Our approach shows that the relevant observables are  $\Sigma_M - 1$  and  $\Gamma_M - 1$  instead of the raw values of the stress maximum coordinates. In that framework, our model yields a quantitative prediction for the rate dependence of the overshoot in the form of two power-law scalings in the limits of low and high shear rates, which may apply to a vast amount of data from the literature—see companion paper [39] for additional comparisons with previous experimental and numerical results [19,21,28,43]. Nonlocal effects play a key role in the predicted scalings by governing the growth of the shear band nucleated in the vicinity of the moving wall: depending on the strain rate, fluidization is driven either by diffusive dynamics or by front propagation. This scenario provides an alternative to existing descriptions of the stress overshoot in terms of local rearrangements and cage dynamics [9,26,28] and to continuum viscoelastic models based on recoverable strain measurements or mean-field

elastoplastic models [6,44–46]. As also emphasized in the companion paper [39], SGMs forming permanent shear bands can be captured within a generalized version of our fluidity model. We show that such a generalization does not affect the scaling properties of the overshoot and that further including long-range correlations into the model and playing with boundary conditions can account for avalanchelike effects as well as brittlelike vs ductilelike response past the overshoot. In that respect, our results should set a basis for predicting shear startup flow in a wide variety of SGMs.

The authors thank David Tamarii for help with the experiments. This research was supported in part by the National Science Foundation under Grant No. NSF PHY-1748958 through the KITP program on the Physics of Dense Suspensions. This work received funding from the European Research Council (ERC) under the European Union’s Horizon 2020 research and innovation programme (Grant Agreement No. 882340).

- 
- [1] D. Rodney, A. Tanguy, and D. Vandembroucq, *Model. Simul. Mater. Sci. Eng.* **19**, 083001 (2011).
- [2] M. Siebenbürger, M. Ballauff, and T. Voigtmann, *Phys. Rev. Lett.* **108**, 255701 (2012).
- [3] C. J. Dimitriou and G. H. McKinley, *Soft Matter* **10**, 6619 (2014).
- [4] D. Bonn, M. M. Denn, L. Berthier, T. Divoux, and S. Manneville, *Rev. Mod. Phys.* **89**, 035005 (2017).
- [5] Y. Joshi and G. Petekidis, *Rheol. Acta* **57**, 521 (2018).
- [6] M. Ozawa, L. Berthier, G. Biroli, A. Rosso, and G. Tarjus, *Proc. Natl. Acad. Sci. U.S.A.* **115**, 6656 (2018).
- [7] T. Divoux, C. Barentin, and S. Manneville, *Soft Matter* **7**, 9335 (2011).
- [8] A. Mohraz and M. Solomon, *J. Rheol.* **49**, 657 (2005).
- [9] N. Koumakis, M. Laurati, S. U. Egelhaaf, J. F. Brady, and G. Petekidis, *Phys. Rev. Lett.* **108**, 098303 (2012).
- [10] J. Zausch, J. Horbach, M. Laurati, S. Egelhaaf, J. Brader, T. Voigtmann, and M. Fuchs, *J. Phys. Condens. Matter* **20**, 404210 (2008).
- [11] M. Laurati, P. Maßhoff, K. J. Mutch, S. U. Egelhaaf, and A. Zacccone, *Phys. Rev. Lett.* **118**, 018002 (2017).
- [12] M. Whittle and E. Dickinson, *J. Chem. Phys.* **107**, 10191 (1997).
- [13] J. Park and K. Ahn, *Soft Matter* **9**, 11650 (2013).
- [14] P. Santos, O. Campanella, and M. Carignano, *Soft Matter* **9**, 709 (2013).
- [15] A. Magnin and J. Piau, *J. Non-Newtonian Fluid Mech.* **36**, 85 (1990).
- [16] J. Persello, A. Magnin, J. Chang, J. Piau, and B. Cabane, *J. Rheol.* **38**, 1845 (1994).
- [17] T. Divoux, D. Tamarii, C. Barentin, and S. Manneville, *Phys. Rev. Lett.* **104**, 208301 (2010).
- [18] R. L. Moorcroft, M. E. Cates, and S. M. Fielding, *Phys. Rev. Lett.* **106**, 055502 (2011).
- [19] C. Amann, M. Siebenbürger, M. Krüger, F. Weysser, M. Ballauff, and M. Fuchs, *J. Rheol.* **57**, 149 (2013).
- [20] C. Derec, G. Ducouret, A. Ajdari, and F. Lequeux, *Phys. Rev. E* **67**, 061403 (2003).
- [21] V. Carrier and G. Petekidis, *J. Rheol.* **53**, 245 (2009).
- [22] N. Koumakis and G. Petekidis, *Soft Matter* **7**, 2456 (2011).
- [23] M. Utz, P. G. Debenedetti, and F. H. Stillinger, *Phys. Rev. Lett.* **84**, 1471 (2000).
- [24] J. Colombo and E. Del Gado, *J. Rheol.* **58**, 1089 (2014).
- [25] A. Zacccone, P. Schall, and E. M. Terentjev, *Phys. Rev. B* **90**, 140203(R) (2014).
- [26] F. Khabaz, B. F. Di Dio, M. Cloitre, and R. T. Bonnecaze, *J. Rheol.* **65**, 241 (2021).
- [27] J. Rottler and M. O. Robbins, *Phys. Rev. E* **68**, 011507 (2003).
- [28] F. Varnik, L. Bocquet, and J.-L. Barrat, *J. Chem. Phys.* **120**, 2788 (2004).
- [29] J. Rottler and M. O. Robbins, *Phys. Rev. Lett.* **95**, 225504 (2005).
- [30] G. P. Shrivastav, P. Chaudhuri, and J. Horbach, *J. Rheol.* **60**, 835 (2016).
- [31] L. C. Johnson, B. J. Landrum, and R. N. Zia, *Soft Matter* **14**, 5048 (2018).
- [32] L. Bocquet, A. Colin, and A. Ajdari, *Phys. Rev. Lett.* **103**, 036001 (2009).
- [33] R. Benzi, M. Sbragaglia, M. Bernaschi, S. Succi, and F. Toschi, *Soft Matter* **12**, 514 (2016).
- [34] R. Benzi, T. Divoux, C. Barentin, S. Manneville, M. Sbragaglia, and F. Toschi, *Phys. Rev. Lett.* **123**, 248001 (2019).
- [35] J. Goyon, A. Colin, G. Ovarlez, A. Ajdari, and L. Bocquet, *Nature (London)* **454**, 84 (2008).
- [36] J. Goyon, A. Colin, and L. Bocquet, *Soft Matter* **6**, 2668 (2010).
- [37] B. Geraud, L. Bocquet, and C. Barentin, *Eur. Phys. J. E* **36**, 30 (2013).
- [38] B. Géraud, L. Jorgensen, C. Ybert, H. Delanoë-Ayari, and C. Barentin, *Eur. Phys. J. E* **40**, 5 (2017).
- [39] R. Benzi, T. Divoux, C. Barentin, S. Manneville, M. Sbragaglia, and F. Toschi, companion paper, *Phys. Rev. E* **104**, 034612 (2021).
- [40] See the Supplemental Material at <http://link.aps.org/supplemental/10.1103/PhysRevLett.127.148003> for a description of the experimental details, including flow curves and stress responses for 2% and 3% Carbopol microgels.
- [41] S. Manneville, L. Bécu, and A. Colin, *Eur. Phys. J. A* **28**, 361 (2004).
- [42] The general derivation shows that  $\lambda = (3 + n)/(6 - 2n)$  and  $\mu = 2n/(3 - n)$ , where  $n$  is the HB exponent. In the case  $n = 1/2$ , one has  $\lambda = 0.7$  and  $\mu = 0.4$  as used for rescaling the strain and stress in Fig. 2(b). See companion paper for details [39].
- [43] R. R. Fernandes, D. E. V. Andrade, A. T. Franco, and C. O. R. Negrão, *J. Rheol.* **61**, 893 (2017).
- [44] G. J. Donley, P. K. Singh, A. Shetty, and S. A. Rogers, *Proc. Natl. Acad. Sci. U.S.A.* **117**, 21945 (2020).
- [45] P. K. Singh, J. C.-W. Lee, and K. A. Patankar, and S. A. Rogers, *J. Rheol.* **65**, 129 (2021).
- [46] K. Kamani, G. J. Donley, and S. A. Rogers, *Phys. Rev. Lett.* **126**, 218002 (2021).