

Effective Oxidation of (5-Hydroxymethyl)furfural to 2,5-Diformylfuran by an Acetal Protection Strategy

Citation for published version (APA):

Boonyakarn, T., Wiesfeld, J. J., Asakawa, M., Chen, L., Fukuoka, A., Hensen, E. J. M., & Nakajima, K. (2022). Effective Oxidation of (5-Hydroxymethyl)furfural to 2,5-Diformylfuran by an Acetal Protection Strategy. *ChemSusChem*, 15(7), Article e202200059. <https://doi.org/10.1002/cssc.202200059>

Document license:
TAVERNE

DOI:
[10.1002/cssc.202200059](https://doi.org/10.1002/cssc.202200059)

Document status and date:
Published: 07/04/2022

Document Version:
Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

Please check the document version of this publication:

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

www.tue.nl/taverne

Take down policy

If you believe that this document breaches copyright please contact us at:

openaccess@tue.nl

providing details and we will investigate your claim.

Effective Oxidation of 5-Hydroxymethylfurfural to 2,5-Diformylfuran by an Acetal Protection Strategy


Tat Boonyakarn,^[a] Jan J. Wiesfeld,^[a] Miyuki Asakawa,^[a] Lulu Chen,^[b] Atsushi Fukuoka,^[a] Emiel J. M. Hensen,^[b] and Kiyotaka Nakajima*^[a]

An acetal protection strategy for 5-hydroxymethylfurfural (HMF) was used to obtain 2,5-diformylfuran (DFF) using concentrated HMF solutions and a γ -Al₂O₃-supported Ru catalyst (Ru/ γ -Al₂O₃). The HMF-acetal with 1,3-propanediol can be oxidized to DFF-acetal with a yield of 84.0% at an HMF conversion of 94.2% from a 50 wt% solution. In contrast, aerobic oxidation of nonprotected HMF using a 10 wt% solution afforded DFF only in a moderate yield (52.3%). Kinetic studies indicated that the six-membered ring acetal group not only prevents side

reactions but also accelerates aerobic oxidation of the –CH₂OH moiety to –CHO under retention of the acetal functionality. Organic deposits formed during the reaction explained the significant decrease in the activity of the Ru/ γ -Al₂O₃ catalyst, which could be recovered neither by washing in water or organic solvents, nor by a calcination-reduction treatment. Sonication of the used Ru/ γ -Al₂O₃ catalyst in an aqueous NaOH solution successfully removed the deposits and allowed reuse of the catalyst for at least four times without activity loss.

Introduction

Lignocellulosic biomass is widely regarded as an abundant, easily accessible, and renewable carbon resource that can replace fossil fuels.^[1,2] Catalytic valorization of its main constituents (cellulose, hemicellulose, and lignin) into platform molecules has been extensively studied to realize sustainable production of fuels and commodity chemicals.^[3–7] Hydrolysis of cellulose into glucose and its subsequent dehydration lead to 5-hydroxymethylfurfural (HMF),^[8–14] which is a versatile intermediate for production of a wide range of chemicals and fuel additives. Scheme 1 presents reaction pathways for the conversion of HMF to intermediates that can be used as monomers for manufacture of polymers with a reduced carbon footprint. Aerobic oxidation of the two functional groups in HMF affords 2,5-furandicarboxylic acid (FDCA),^[15–19] while hydrogenation of HMF yields 2,5-bis(hydroxymethyl)furan (BHMF)^[20–23] and 2,5-bis(hydroxymethyl)tetrahydrofuran (BHMTHF).^[24–28] BHMTHF can be further transformed to aliphatic alcohols such as 1,6-hexanediol and 1,2,6-hexanetriol, and 1,6-hexanediol is a source of adipic acid.^[24,29–31] Partial oxidation of HMF can also lead to 2,5-diformylfuran (DFF), which can be further converted to 2,5-bis(aminomethyl)furan (AMF).^[32–36] Although AMF has substantial potential as a building block for polyamides,^[37,38] efficient

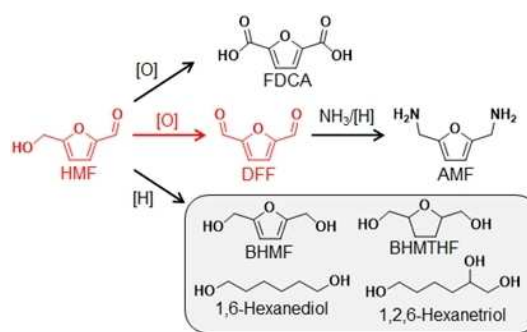

Scheme 1. Reaction pathways to several valuable monomers obtainable from HMF.

synthetic procedures have not yet been developed. For the first step of AMF production, we have studied aerobic oxidation of the hydroxymethyl group in HMF to the corresponding formyl group using supported metal catalysts and concentrated solutions (Scheme 1).

Reaction paths for the aerobic oxidation of HMF to FDCA in water are illustrated in Scheme S1. The formyl group is easily oxidized to the corresponding carboxylic acid in water via the formation of a geminal diol intermediate. HMF can be easily oxidized to FDCA through 5-(hydroxymethyl)furan-2-carboxylic acid (HMFCA) and 5-formylfuran-2-carboxylic acid (FFCA) as intermediates, while DFF is only obtained in very small amounts. The use of non-protic organic solvents such as toluene and *N,N'*-dimethylformamide (DMF) prevents the hydration of the formyl group to a geminal diol (Scheme S1) and its subsequent oxidative dehydrogenation to a carboxylic acid. This provides an opportunity to selectively oxidize HMF to DFF. Supported noble metal catalysts such as Pt, Pd, Au, or Ru have been extensively studied for the selective oxidation of HMF in toluene and DMF as shown in Table S1.^[39–48] Other catalysts reported to be active for DFF formation include metal oxides

[a] T. Boonyakarn, Dr. J. J. Wiesfeld, M. Asakawa, Prof. Dr. A. Fukuoka, Prof. Dr. K. Nakajima
Institute for Catalysis
Hokkaido University
Kita 21 Nishi 10, Kita-ku, Sapporo
001-0021 (Japan)
E-mail: nakajima@cat.hokudai.ac.jp

[b] L. Chen, Prof. Dr. E. J. M. Hensen
Laboratory of Inorganic Chemistry and Catalysis
Department of Chemical Engineering and Chemistry
Eindhoven University of Technology
PO Box 513, 5600 MB Eindhoven (The Netherlands)

Supporting information for this article is available on the WWW under <https://doi.org/10.1002/cssc.202200059>

containing Mn, V, Cu, Co, and Fe,^[49–53] while also metal-free and nitrogen-doped carbon catalysts show significant potential for this reaction.^[54] Despite high DFF yields, all reactions in the previous works were only studied using dilute HMF solutions (< 10 wt% HMF) as shown in Table S1. This is most likely due to severe byproduct formation, which proceeds predominantly in concentrated solutions as exemplified in the aerobic oxidation of 10 wt% HMF in water and methanol over a CeO₂-supported Au catalyst.^[55,56]

By-product formation is a serious issue for the catalytic valorization of lignocellulose biomass, which cannot be simply controlled by optimization of the reaction conditions (temperature, substrate concentration, type of catalyst, etc). To suppress by-product formation in concentrated solutions, we have developed a protection strategy of the highly reactive formyl group in HMF with 1,3-propanediol.^[55,56] Acetalization of the formyl group with 1,3-propanediol forms a six-membered ring acetal, which shows high stability against side reactions during aerobic oxidation and oxidative esterification to synthesize FDCA and its alkyl carboxylate derivatives. Such protection strategies are recently regarded to be effective for biomass conversion as biomass-derived intermediates usually have highly reactive functional groups that are easily involved in side reactions.^[57–61]

Herein, we employed the acetal protection strategy for the selective production of DFF from HMF. We oxidized the acetal form of HMF with 1,3-propanediol (HMF-acetal) using carbon-, γ -Al₂O₃-, ZrO₂-, and hydrotalcite (HT)-supported Ru catalysts in DMF as a solvent, because the combination of supported Ru catalysts and DMF has been effective for selective DFF formation (> 90% selectivity) in dilute HMF solutions (Table S1).^[39,44,45] HMF and HMF-acetal in various concentrations (10–70 wt%) were oxidized to clarify the effect of the acetal functionality on the product distribution. Kinetic studies were used to evaluate the electron-donating effect of the acetal functionality toward the oxidation rate for –CH₂OH by comparison with other reference furan compounds. Furthermore, a regeneration strategy was developed for the used Ru catalyst.

Results and Discussion

Aerobic oxidation of HMF and HMF-acetal

A previous study^[39] reported that inert or weakly amphoteric supports are well-suited for HMF oxidation to DFF as HMF degrades rapidly in contact with strongly acidic or basic supports, and Ru/C is found to be the most optimal catalyst. In this paper, we also prepared supported Ru catalysts with inert (C and SiO₂) and amphoteric oxide (γ -Al₂O₃, HT, and ZrO₂) supports and examined them in aerobic oxidation of HMF-acetal. All supported Ru catalysts were characterized by X-ray diffraction (XRD) (Figure S1). No distinct diffraction features related to Ru were observed for Ru/ γ -Al₂O₃ and Ru/C (Figure S1B, E), while Ru/SiO₂, Ru/HT, and Ru/ZrO₂ exhibited broad features assignable to metallic Ru (Figure S1A, C, D). The former samples likely contain highly dispersed and metallic Ru nano-

particles, which cannot be detected by XRD due to their small size. The average size of the metallic Ru nanoparticles in Ru/SiO₂, Ru/HT, and Ru/ZrO₂, estimated by use of the Scherrer equation using the Ru (101) reflection, was 3.8, 6.3, and 12.3 nm, respectively. The original layered structure of the HT support was completely lost during the reduction step (Figure S1C).^[62] The XRD pattern of the resulting Ru/HT catalyst did not contain features associated with the original HT support, which means that the Ru nanoparticles are situated on a mixed oxide of MgO and Al₂O₃.

These catalysts were preliminarily examined in aerobic oxidation of the HMF-acetal using a 10 wt% HMF-acetal solution (Figure S2). Here, Ru/ γ -Al₂O₃ vastly outperformed Ru/C, which differs from the results reported by the previous study.^[39] Ru/ZrO₂, Ru/SiO₂, and Ru/HT performed fairly equal in terms of DFF yield and selectivity, but these three catalysts were also less active than Ru/ γ -Al₂O₃. The lower activities of Ru/ZrO₂, Ru/SiO₂, and Ru/HT can instead be explained by the difference in Ru particle size. Average particle sizes of Ru/SiO₂, Ru/HT, and Ru/ZrO₂ were 3.8–12.3 nm, which were all significantly larger than that of Ru/ γ -Al₂O₃ (Figure S3A, \approx 1.5 nm estimated by transmission electron microscopy (TEM) observation). Ru/ γ -Al₂O₃ was therefore selected for further optimization studies. DMF was also selected as an appropriate solvent and used throughout this study (see a solvent screening in page S6 of the Supporting Information).

Ru/ γ -Al₂O₃ was used to examine the performance in the aerobic oxidation of HMF and HMF-acetal as a function of the substrate concentration. The oxidation reaction was conducted at 383 K for 300 min in DMF under 0.5 MPa O₂ pressure with a substrate/Ru ratio of 20 w/w. Table 1 summarizes the catalytic performance data at various HMF-acetal concentrations (entries 1–4). All acetal moieties were completely removed from the reaction products (DFF-acetal and FFCA-acetal) and the substrate (HMF-acetal) during HPLC analysis involving the use of a diluted H₂SO₄ eluent.^[55] However, kinetic studies in the following section, in which analysis relied on a combination of high-performance liquid chromatography (HPLC) and proton nuclear magnetic resonance (¹H NMR) spectroscopy, revealed that deprotection of HMF-acetal under the given reaction conditions was negligible. This means that DFF and FFCA were only present in their acetal form during the reaction. For the sake of brevity, the yields of DFF-acetal and FFCA-acetal are nevertheless expressed as “DFF yield” and “FFCA yield” in Table 1. The conversion values estimated by HPLC therefore reflect the HMF-acetal conversion. Ru/ γ -Al₂O₃ afforded DFF in 77.6% yield at 90.4% conversion in a 10 wt% HMF-acetal solution (entry 1). FFCA was obtained as a minor product in a yield of only 2.7%, which means that the oxidation of the formyl group in DFF is effectively suppressed under the given reaction conditions, which is due to the absence of water in the reaction medium (Scheme S1). High DFF yields (\approx 80%) could also be obtained in 30 and 50 wt% solutions (entries 2 and 3). The difference between HMF-acetal conversion and the sum of identified products (DFF and FFCA) is very small in these experiments, indicating that the amount of oligomerized products that cannot be detected was very low, even at an

Table 1. Aerobic oxidation of HMF and HMF-acetal over supported Ru catalysts.^[a]

Entry	Substrate	Concentration [wt%]	Conversion [%]	Product yield [%]			Carbon balance [%]
				DFF	FFCA	By-products	
1	HMF-acetal	10	90.4 ± 8.0	77.6 ± 5.3	2.7 ± 0.2	10.1 ± 3.0	89.9 ± 3.0
2		30	95.0 ± 3.0	79.3 ± 1.9	2.6 ± 0.6	13.1 ± 4.0	86.9 ± 4.0
3		50	94.2 ± 1.0	84.0 ± 1.8	2.6 ± 0.3	7.6 ± 1.0	92.4 ± 1.0
4	HMF	70	96.7 ± 1.8	53.3 ± 1.4	1.9 ± 1.2	41.5 ± 0.9	58.5 ± 0.9
5		10	96.4 ± 1.8	52.3 ± 1.5	15.1 ± 2.8	29.0 ± 1.3	71.0 ± 1.3
6		30	93.1 ± 4.8	53.3 ± 3.0	14.5 ± 4.1	25.3 ± 1.1	74.7 ± 1.1
7		50	91.2 ± 1.1	21.2 ± 2.0	6.7 ± 2.9	63.3 ± 5.0	36.7 ± 5.0
8		70	99.4 ± 1.1	4.6 ± 2.3	0.4 ± 0.9	94.4 ± 3.1	5.6 ± 3.1

[a] Reaction conditions: substrate, HMF-acetal or HMF (0.1–0.7 g); solvent, DMF (0.3–0.9 g); catalyst, Ru/ γ -Al₂O₃ (substrate/Ru ratio: 20 w/w); oxygen pressure, 0.5 MPa; temperature, 383 K; time, 300 min.

HMF-acetal concentration as high as 50 wt%. However, a further increase in the HMF-acetal concentration to 70 wt% (entry 4) led to a lower DFF yield of 53.3% with a large increase in by-product yield (41.5%). When HMF-acetal was replaced by HMF, the dependence of the product distribution on substrate concentration was very different. DFF yield was moderate (52.3%) at an HMF concentration of only 10 wt% (entry 5). The formation of FFCA in 15.1% yield and a large amount of undetectable by-products in 29.0% yield point to substantial contributions of the over-oxidation of the formyl group in DFF and condensation reactions of HMF and DFF into oligomerized by-products. While similar results were obtained in a 30 wt% HMF solution (entry 6), the formation of by-products became dominant upon a further increase of the HMF concentration, affording DFF yields of 21.2% at 50 wt% substrate concentration (entry 7) and 4.6% at 70 wt% substrate concentration (entry 8). These results demonstrate that the protection of formyl moiety with 1,3-propanediol can facilitate the selective synthesis of DFF in concentrated solutions.^[55] HMF-acetal provided significant advantage in DFF formation using concentrated solutions compared to HMF. However, the values of carbon balance are approximately 90% (entries 1–3), which is due to humin-type by-product formation. Such by-products are stabilized on the catalyst surface and influence the reusability of the Ru/Al₂O₃ catalyst (vide infra).

Kinetic studies on aerobic oxidation of HMF and HMF-acetal

Reaction pathways for the oxidation of HMF and HMF-acetal were investigated at 383 K under 0.5 MPa O₂ atmosphere using Ru/ γ -Al₂O₃ as the catalyst and a substrate concentration of 50 wt%. Figure 1 shows time courses for HMF conversion and product yields. Kinetic traces were fitted using pseudo-first order-reaction kinetics. HMF was oxidized to DFF, while the further conversion of DFF to FFCA was small. The reaction rate constant for DFF formation ($k_1 = 0.84 \text{ h}^{-1}$) is much larger than that for FFCA formation ($k_2 = 0.05 \text{ h}^{-1}$). Oxidation of the formyl group to the carboxylic acid is largely suppressed under the given reaction conditions as evidenced by the absence of HMFCFA and FDCA as well as by the very small amount of FFCA formed (see Scheme S1). The high selectivity to DFF can be explained by the aprotic nature of the DMF solvent, which

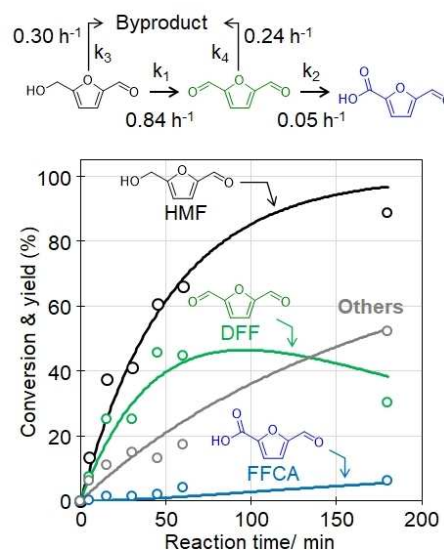


Figure 1. Time course for DFF formation from HMF: HMF, 0.5 g; DMF, 0.5 g; Ru/ γ -Al₂O₃ catalysts, 0.5 g (substrate/Ru ratio: 20 w/w); oxygen pressure, 0.5 MPa; temperature, 383 K.

prevents the hydration of the aldehyde moiety to the geminal diol intermediate prior to its oxidation to the corresponding carboxylic acid (Scheme S1).^[63] The DFF yield reached a maximum after 60 min and then decreased gradually with time, accompanied by increasing levels of oligomerized byproducts. Fitting of the kinetic traces suggests that these byproducts are formed from both HMF and DFF with similar reaction rate constants, that is, 0.30 h^{-1} (k_3) and 0.24 h^{-1} (k_4), respectively.

By-product formation in HMF oxidation was further evaluated by carrying out two control experiments (Table S2). The reactions were conducted at 383 K for 30 min in the presence of Ru/ γ -Al₂O₃ in an inert atmosphere (0.5 MPa N₂) using either a 50 wt% HMF solution or a 50 wt% DFF solution. Approximately 60% of HMF was converted to undetectable by-product through non-oxidative side reactions (Table S2, entry 1). In contrast, DFF loss under the same reaction conditions was limited to 18.8% (Table S2, entry 2), despite there being no large difference between the rate constants for by-product formation from HMF and DFF (i.e., k_3 and k_4 in aerobic HMF oxidation, Figure 1). These results imply that DFF degradation is

more pronounced under oxidative reaction conditions or in the presence of HMF.

Figure 2 shows time courses for HMF-acetal conversion and product yields, in which kinetic traces were also fitted using pseudo-first order-reaction kinetics. Quantitative analysis using ^1H NMR demonstrated that HMF and DFF are present in the acetal form in all reaction mixtures (Figure S4). HMF-acetal conversion and DFF-acetal yield continuously increased with time and reached 81.3 and 73.5% at 60 min and 93.0 and 84.2% at 180 min, respectively. By-product formation mainly took place in the initial stage of the reaction (8.8% yield at 30 min) and did not change much afterwards. Oxidation of the formyl group in DFF-acetal hardly proceeded as evident from the small reaction rate constant for FFCA-acetal formation ($k_6 = 0.006\text{ h}^{-1}$), which is an order of magnitude lower than that for FFCA formation in HMF oxidation ($k_2 = 0.05\text{ h}^{-1}$). The acetal moieties in HMF-acetal and DFF-acetal effectively prevent undesired side reactions that lead to condensed products. DFF-acetal was fully retained in the reaction mixture, whereas degradation of free DFF occurred in HMF oxidation ($k_4 = 0.24\text{ h}^{-1}$ in Figure 1). By-product formation from HMF-acetal ($k_7 = 0.18\text{ h}^{-1}$) is approximately half that from HMF ($k_3 = 0.30\text{ h}^{-1}$). Thermal degradation of HMF-acetal and DFF-acetal was also evaluated under an inert atmosphere (Table S2). When the same reactions in entries 1 and 2 of Table S2 were conducted using HMF-acetal and DFF-acetal, both showed very low conversion (<2%) and minor levels of degradation (entries 3 and 4).

It should be noted that the rate constant for DFF-acetal formation ($k_5 = 1.5\text{ h}^{-1}$, Figure 2) is approximately two times higher than that of DFF formation ($k_1 = 0.84\text{ h}^{-1}$, Figure 1). Such a large difference can explain the efficient production of DFF-acetal in the aerobic oxidation of HMF-acetal. To understand the increase in the reaction rate constant for the oxidation of $-\text{CH}_2\text{OH}$ to $-\text{CHO}$ in the presence of the acetal functional

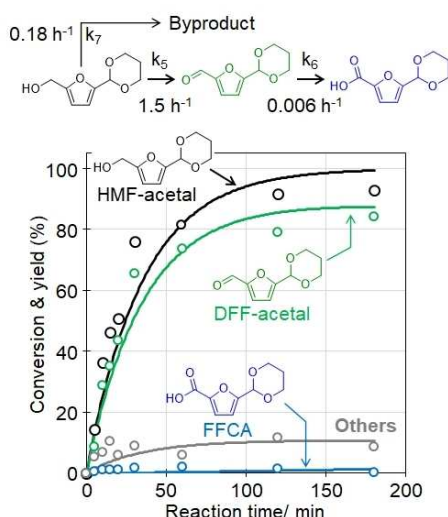


Figure 2. Time course for DFF-acetal formation from HMF-acetal: HMF-acetal, 0.5 g; DMF, 0.5 g; Ru/ $\gamma\text{-Al}_2\text{O}_3$ catalysts, 0.5 g (substrate/Ru ratio: 20 w/w); oxygen pressure, 0.5 MPa; temperature, 383 K.

group, we selected two additional substrates, namely HMFCa and furfuryl alcohol. We compared the effect of the functional group (carboxylic acid in HMFCa, hydrogen in furfuryl alcohol, formyl group in HMF, and six-membered acetal group in HMF-acetal) against aerobic oxidation of the hydroxymethyl group over Ru/ $\gamma\text{-Al}_2\text{O}_3$ (Figures 1, 2, S5, and S6). Figure 3 summarizes rate constants for a series of substrates. The rate constant for HMF-acetal oxidation is larger (1.5 h^{-1}) compared to oxidation rate constants for furfuryl alcohol (1.2 h^{-1}), HMF (0.84 h^{-1}), and HMFCa (0.03 h^{-1}). There is a correlation between the rate constant and the electron-donating/-withdrawing nature of the functional group. The rate constants were relatively large for the electron-donating acetal functional group in the HMF-acetal. The rate constants decreased with increasing electron-withdrawing character of the functional group (electron-withdrawing property: $-\text{COOH}$ in HMFCa $>$ $-\text{CHO}$ in HMF $>$ $-\text{H}$ in furfuryl alcohol). The presence of electron-donating group most probably facilitated the dissociation of OH and/or CH bonds in $-\text{CH}_2\text{OH}$ attached to furan ring and enhanced efficient aerobic oxidation to formyl group. A similar effect was observed for the photo-oxidation of substituted benzyl alcohols to benzaldehyde.^[64]

In sharp contrast to alcohol oxidation ($-\text{CH}_2\text{OH}$), similar reaction rate constants were obtained for aldehyde oxidation to carboxylic acid in three substrates (HMF-acetal, $k_6 = 0.006\text{ h}^{-1}$ in Figure 2; HMFCa, $k_2 = 0.006\text{ h}^{-1}$ in Figure S5; furfuryl alcohol, $k_2 = 0.006\text{ h}^{-1}$ in Figure S6), suggesting no influence of the type of functional group on the reaction rate constant. The formation of carboxylic acid from aldehyde under the reaction conditions requires water to produce geminal diol intermediate as shown in Scheme S1. All oxidation reactions were conducted in non-aqueous solutions, which successfully suppressed undesirable oxidation to the carboxylic acid. Aldehyde oxidation to carboxylic acid forming FFCA (Figure 1) is also nearly absent during HMF oxidation, but its rate constant ($k_2 = 0.05\text{ h}^{-1}$) is an order of magnitude higher than for the other three substrates. Relatively large reaction rate constant in HMF oxidation is maybe attributed to water formation in pronounced side reactions leading to the formation of undesirable carboxylic

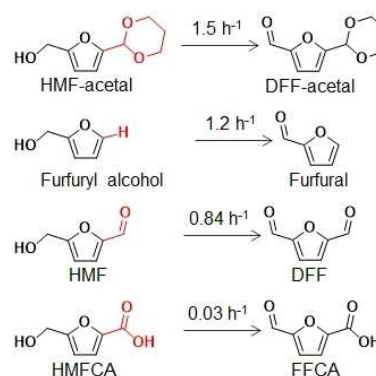


Figure 3. Rate constants for HMF-acetal and reference compounds (furfuryl alcohol, HMF, and HMFCa) in aerobic oxidation: substrate, 0.5 g; DMF, 0.5 g; Ru/ $\gamma\text{-Al}_2\text{O}_3$ catalysts, 0.5 g (substrate/Ru ratio: 20 w/w); oxygen pressure, 0.5 MPa; temperature, 383 K.

acid by the oxidation of geminal diol intermediate as shown in Scheme S1.

Catalyst regeneration

The regeneration of Ru/ γ -Al₂O₃ was investigated in the oxidation of HMF-acetal using concentrated solutions (50 wt%), where all reactions were conducted at 383 K for 60 min under 0.5 MPa O₂. After the reaction, the catalyst was recovered by filtration, washed with water (\approx 50 mL), dried at 373 K in air overnight, and then used again in the same reaction (Figure 4A). The DFF-acetal yield decreased from 73.5 to 37.0% in the second run and further to 7.8% in the fifth run. The XRD patterns of fresh and used Ru/ γ -Al₂O₃ were similar (Figure S7a, b), implying that catalyst deactivation is not caused by Ru particle growth. It is more likely that deposition of humins blocks part of the surface.^[45,65] Humin build-up was confirmed by thermogravimetry-differential thermal analysis (TG-DTA) of the used Ru/ γ -Al₂O₃, which exhibits a weight loss of approximately 15% in the 423–673 K range (Figure S8B). The used catalyst after the fourth reuse was calcined at 773 K for 2 h in air to remove the deposits and reduced at 673 K for 2 h in an H₂

flow (10 mLmin⁻¹). This treatment was not effective for the recovery of the original activity. The thus-regenerated catalyst gave a DFF yield of only 5.5% at a conversion of 23.8% in the sixth run under the same reaction conditions. XRD showed that the calcination-reduction treatment leads to growth of Ru nanoparticles (Figure S7c), which results in the production of large amounts of undetectable byproduct (18.2%).

Washing with organic solvent mixtures containing acetone, ethanol, and toluene was equally ineffective in removing the humin depositions and recovering original activity (Table S3). Sonication in NaOH solution was therefore adopted to remove organic deposits from the surface of Ru nanoparticles.^[45] The used catalyst was dispersed in an aqueous NaOH solution (pH = 12, 50 mL) and sonicated at room temperature for 10 min. This treatment was repeated three times with refreshing the solution at every cycle. After the final step, the catalyst was recovered by filtration, washed with water, dried in an oven overnight, and then used again in the DFF-acetal oxidation reaction. Figure 4B shows the catalytic activities of fresh and regenerated Ru/ γ -Al₂O₃ catalysts. The HMF-acetal conversion of 70–80% and DFF-acetal selectivity of approximately 80% were maintained for five cycles. We also characterized the 4-times reused Ru/ γ -Al₂O₃ catalyst after regeneration by TG-DTA, XRD, TEM, and X-ray photoelectron spectroscopy (XPS). The TG-DTA profile of the used catalyst in Figure S8C is similar to that of the fresh catalyst in Figure S8A, showing that the NaOH treatment is effective in removing organic deposits. The XRD patterns of fresh and used-generated catalysts in Figure S7a, d demonstrate that the NaOH treatment did not lead to Ru nanoparticle growth. This finding is also corroborated by TEM analysis of fresh and used catalysts, showing a predominance of 1–2 nm sized Ru nanoparticles in both catalysts (Figure S3). The oxidation state of Ru nanoparticle for fresh and used catalysts was investigated by XPS (Figure S9). There was no significant difference in the ratio of metallic Ru and oxidized Ru (Ruⁿ⁺) between fresh and used catalysts (Table S4). Finally, leaching of oxidized Ru species during the regeneration treatment using NaOH solutions was evaluated by inductively coupled plasma atomic emission spectroscopy (ICP-AES) analysis. NaOH solutions after sonication with the used catalyst contained only trace level of Ru (\approx 0.005%), demonstrating that leaching of the supported Ru nanoparticles is nearly negligible. All these results evidence that aerobic oxidation of HMF-acetal with 1,3-propanediol using Ru/ γ -Al₂O₃ is a promising strategy for the efficient and scalable production of DFF in excellent yields using concentrated solutions.

Conclusion

A facile reaction system to produce DFF from HMF was developed using concentrated HMF-acetal solutions and a Ru/ γ -Al₂O₃ catalyst. Acetal protection of the formyl group in HMF prevents side reactions in concentrated solutions during aerobic oxidation. Under optimized conditions, HMF-acetal was oxidized at a concentration of 50 wt% in DMF using Ru/ γ -Al₂O₃ at an HMF-acetal/Ru mass ratio of 20 at 383 K under 0.5 MPa O₂

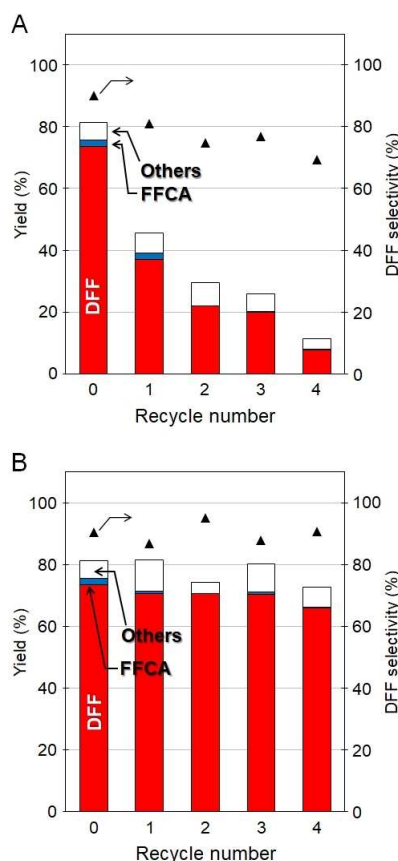


Figure 4. Recyclability of Ru/ γ -Al₂O₃ catalyst in aerobic oxidation of HMF-acetal using 50 wt% solutions: (A) washing with water and (B) sonication in aqueous NaOH (pH = 12) solution. Reaction conditions: HMF-acetal, 0.5 g; DMF, 0.5 g; Ru/ γ -Al₂O₃ catalysts, 0.5 g (substrate/Ru ratio: 20 w/w); oxygen pressure, 0.5 MPa; temperature, 383 K; time, 60 min.

pressure. After 5 h, a high DFF yield of 84.0% was obtained. Under comparable conditions, oxidation of HMF yielded only 21.2% of DFF. Deposition of humin-type organic compounds during the reactions resulted in a substantial decrease of the original activity of Ru/ γ -Al₂O₃ in reuse experiments. Sonication of the used catalyst in NaOH solution removed the deposits and fully recovered the activity, allowing efficient regeneration for at least 4 times without significant loss of activity. DFF production using concentrated solutions in this study is significantly distinct from those in previous reports in terms of productivity as well as the energy consumption for the work-up process. The benefits of working with concentrated substrate solutions are a smaller reactor size and lower energy cost for recycling the organic solvent by evaporation and distillation. Thus, a novel chemocatalytic route to DFF, which is a precursor to building blocks for polyamides and polyesters, has been developed.

Experimental Section

Materials

Ru/ γ -Al₂O₃, DMF, HT, and ZrO₂ were purchased from FUJIFILM Wako Pure Chemical Corporation. HMF, 2-furoic acid, and furfural were procured from Sigma-Aldrich. DFF, FFCA, furfuryl alcohol, and FDCA were obtained from Tokyo Chemical Industry. HMFCA was purchased from Combi-Blocks Inc. Ruthenium(III) nitrosyl nitrate solution (1.5 wt% of Ru) was procured from Strem Chemicals. Aerosil-380 (SiO₂) and activated carbon (AC) were obtained from Evonik industries and Ajinomoto Fine-Techno Corporation, respectively.

Catalyst preparation

Ru/HT, Ru/C, Ru/SiO₂, and Ru/ZrO₂ catalysts with Ru loading of 5 wt% were prepared by incipient wetness impregnation using ruthenium(III) nitrosyl nitrate. HT, SiO₂, ZrO₂, or AC was added to an aqueous solution containing ruthenium(III) nitrosyl nitrate precursor. After stirring the mixture at room temperature and subsequent vacuum evaporation of water at 373 K, the solids recovered were dried at 393 K overnight in air and then reduced in H₂ at a flow of (10 mL min⁻¹) at 673 K for 2 h (10 K min⁻¹). Ru/ γ -Al₂O₃ was used as received.

Catalyst characterization

Powder XRD patterns were obtained from an X-ray diffractometer (Rigaku, Ultima IV) using Cu K α radiation (40 kV, 20 mA) over the 2 θ range of 10–90°. Adsorption isotherms were acquired from a Belsorp mini II (Microtrac MRB). The Brunauer–Emmett–Teller (BET) equation was used to estimate the specific surface areas ($P/P_0 = 0.05–0.30$). XPS spectra were acquired using a JEOL JPC-9010MC instrument at pass energy of 20 eV using the Mg K α line. Charge correction was based on the position of C 1s (284.6 eV). TEM images were obtained using a microscope (JEM-2100F JEOL Ltd.) without metal deposition on the sample. Possible metal leaching as a result of the alkaline washing procedure of spent catalysts was analyzed by ICP-AES (ICPE-9000, Shimadzu). TGA were performed on a Rigaku Thermo plus TG 8121 apparatus in the temperature range from room temperature to 1273 K at a heating rate of 10 K min⁻¹ under flowing air (50 mL min⁻¹).

Aerobic oxidation of HMF and HMF-acetal

Catalytic activity was tested in a 10 mL SUS-316 stainless-steel batch reactor equipped with a polytetrafluoroethylene (PTFE) liner. 0.1–0.7 g of the substrate (HMF or HMF-acetal prepared according to a previous paper),^[55] 0.3–0.9 g of DMF, and 0.1–0.7 g of the Ru catalyst were charged into the reactor, which was subsequently pressured with oxygen to 0.5 MPa and heated in an oil bath at 383 K, where substrate/catalyst (Ru) ratio on mass basis were kept constant at 20 in all reactions. After a specified reaction period, the reactor was cooled to room temperature, and products were analyzed by HPLC. The quantification of HMF, DFF, FFCA, and FDCA was conducted by HPLC (SHIMADZU, Japan) consisting of a RID-10A detector, a UV-SPD-20A detector, and an Aminex HPX-87H ion column (column temp., 308 K). A diluted H₂SO₄ solution (5 mM) was used as the eluent at a flow rate of 0.5 mL min⁻¹. The retention times for furfuraldehyde, HMF, furoic acid, DFF, FFCA, HMFCA, FDCA, and furfuryl alcohol were 67.0, 43.3, 42.5, 54.4, 30.0, 27.0, 21.0, and 15.6 min, respectively. As reported in previous papers, HMF-acetal, DFF-acetal, or FFCA-acetal were quantitatively converted to HMF, DFF, or FFCA, respectively, during HPLC measurement.^[55]

Acknowledgements

This work was supported by JST-MIRAI program (Grant number JPMJMI19E3), Japan. A part of this work was also supported by JSPS Grant-in-Aid for Transformative Research Areas (A) "Hyper-Ordered Structures Science (20H05879)", JSPS Fostering Joint International Research (B) (18KK0135), and the Cooperative Research Program of Institute for Catalysis, Hokkaido University (20A1002).

Conflict of Interest

The authors declare no conflict of interest.

Data Availability Statement

Research data are not shared.

Keywords: 5-hydroxymethylfurfural · biomass · diformylfuran · heterogeneous catalysis · oxidation

- [1] J. N. Chheda, G. W. Huber, J. A. Dumesic, *Angew. Chem. Int. Ed.* **2007**, *46*, 7164–7183; *Angew. Chem.* **2007**, *119*, 7298–7318.
- [2] J. J. Bozell, G. R. Petersen, *Green Chem.* **2010**, *12*, 539–55.
- [3] G. W. Huber, S. Iborra, A. Corma, *Chem. Rev.* **2006**, *106*, 4044–4098.
- [4] A. Corma Canos, S. Iborra, A. Velty, *Chem. Rev.* **2007**, *107*, 2411–2502.
- [5] I. Delidovich, P. J. C. Hausoul, L. Deng, R. Pfützenreuter, M. Rose, R. Palkovits, *Chem. Rev.* **2016**, *116*, 1540–1599.
- [6] C. Li, X. Zhao, A. Wang, G. W. Huber, T. Zhang, *Chem. Rev.* **2015**, *115*, 11559–11624.
- [7] F. H. Isikgor, C. R. Becer, *Polym. Chem.* **2015**, *6*, 4497–4559.
- [8] H. Zhao, J. E. Holladay, H. Brown, Z. C. Zhang, *Science* **2007**, *316*, 1597–1600.
- [9] E. A. Pidko, V. Degirmenci, R. A. Van Santen, E. J. M. Hensen, *Angew. Chem. Int. Ed.* **2010**, *49*, 2530–2534; *Angew. Chem.* **2010**, *122*, 2584–2588.

- [10] E. Nikolla, Y. Román-Leshkov, M. Moliner, M. E. Davis, *ACS Catal.* **2011**, *1*, 408–410.
- [11] K. Nakajima, Y. Baba, R. Noma, M. Kitano, J. N. Kondo, S. Hayashi, M. Hara, *J. Am. Chem. Soc.* **2011**, *133*, 4224–4227.
- [12] R. Noma, K. Nakajima, K. Kamata, M. Kitano, S. Hayashi, M. Hara, *J. Phys. Chem. C* **2015**, *119*, 17117–17125.
- [13] C. Yue, G. Li, E. A. Pidko, J. J. Wiesfeld, M. Rigutto, E. J. M. Hensen, *ChemSusChem* **2016**, *9*, 2421–2429.
- [14] G. Li, E. A. Pidko, E. J. M. Hensen, K. Nakajima, *ChemCatChem* **2018**, *10*, 4084–4089.
- [15] O. Casanova, S. Iborra, A. Corma, *ChemSusChem* **2009**, *2*, 1138–1144.
- [16] O. Casanova, S. Iborra, A. Corma, *J. Catal.* **2009**, *265*, 109–116.
- [17] N. K. Gupta, S. Nishimura, A. Takagaki, K. Ebitani, *Green Chem.* **2011**, *13*, 824–827.
- [18] M. Sajid, X. Zhao, D. Liu, *Green Chem.* **2018**, *20*, 5427–5453.
- [19] E. Hayashi, Y. Yamaguchi, K. Kamata, N. Tsunoda, Y. Kumagai, F. Oba, M. Hara, *J. Am. Chem. Soc.* **2019**, *141*, 899–900.
- [20] Y. Takeda, M. Tamura, Y. Nakagawa, K. Okumura, K. Tomishige, *Catal. Sci. Technol.* **2016**, *6*, 5668–5683.
- [21] M. Tamura, K. Tokonami, Y. Nakagawa, K. Tomishige, *Chem. Commun.* **2013**, *49*, 7034–7036.
- [22] S. T. Thompson, H. H. Lamb, *ACS Catal.* **2016**, *6*, 7438–7447.
- [23] J. J. Wiesfeld, M. Kim, K. Nakajima, E. J. M. Hensen, *Green Chem.* **2020**, *22*, 1229–1238.
- [24] T. Buntara, S. Noel, P. H. Phua, I. Melián-Cabrera, J. G. De Vries, H. J. Heeres, *Angew. Chem. Int. Ed.* **2011**, *50*, 7083–7087; *Angew. Chem.* **2011**, *123*, 7221–7225.
- [25] X. Kong, R. Zheng, Y. Zhu, G. Ding, Y. Zhu, Y. W. Li, *Green Chem.* **2015**, *17*, 2504–2514.
- [26] J. Chen, R. Liu, Y. Guo, L. Chen, H. Gao, *ACS Catal.* **2015**, *5*, 722–733.
- [27] Y. Nakagawa, K. Takada, M. Tamura, K. Tomishige, *ACS Catal.* **2014**, *4*, 2718–2726.
- [28] Y. Nakagawa, K. Tomishige, *Catal. Commun.* **2010**, *12*, 154–156.
- [29] S. Yao, X. Wang, Y. Jiang, F. Wu, X. Chen, X. Mu, *ACS Sustainable Chem. Eng.* **2014**, *2*, 173–180.
- [30] T. Buntara, I. Melián-Cabrera, Q. Tan, J. L. G. Fierro, M. Neurock, J. G. De Vries, H. J. Heeres, *Catal. Today* **2013**, *210*, 106–116.
- [31] M. J. Gilkey, A. V. Mironenko, L. Yang, D. G. Vlachos, B. Xu, *ChemSusChem* **2016**, *9*, 3113–3121.
- [32] D. Pingen, J. B. Schwaderer, J. Walter, J. Wen, G. Murray, D. Vogt, S. Mecking, *ChemCatChem* **2018**, *10*, 3027–3033.
- [33] Y. Xu, X. Jia, J. Ma, J. Gao, F. Xia, X. Li, J. Xu, *Green Chem.* **2018**, *20*, 2697–2701.
- [34] K. Zhou, H. Liu, H. Shu, S. Xiao, D. Guo, Y. Liu, Z. Wei, X. Li, *ChemCatChem* **2019**, *11*, 2649–2656.
- [35] G. Liang, A. Wang, L. Li, G. Xu, N. Yan, T. Zhang, *Angew. Chem. Int. Ed.* **2017**, *56*, 3050–3054; *Angew. Chem.* **2017**, *129*, 3096–3100.
- [36] H. Qi, F. Liu, L. Zhang, L. Li, Y. Su, J. Yang, R. Hao, A. Wang, T. Zhang, *Green Chem.* **2020**, *22*, 6897–6901.
- [37] M. Winnacker, B. Rieger, *Macromol. Rapid Commun.* **2016**, *37*, 1391–1413.
- [38] J. M. García, F. C. García, F. Serna, J. L. de la Peña, *Prog. Polym. Sci.* **2010**, *35*, 623–686.
- [39] J. Nie, J. Xie, H. Liu, *J. Catal.* **2013**, *301*, 83–91.
- [40] S. E. Davis, L. R. Houk, E. C. Tamargo, A. K. Datye, R. J. Davis, *Catal. Today* **2011**, *160*, 55–60.
- [41] Y. Zhu, M. Shen, Y. Xia, M. Lu, *Catal. Commun.* **2015**, *64*, 37–43.
- [42] Z. Zhang, Z. Yuan, D. Tang, Y. Ren, K. Lv, B. Liu, *ChemSusChem* **2014**, *7*, 3496–3504.
- [43] D. K. Mishra, J. K. Cho, Y. J. Kim, *J. Ind. Eng. Chem.* **2018**, *60*, 513–519.
- [44] A. Takagaki, M. Takahashi, S. Nishimura, K. Ebitani, *ACS Catal.* **2011**, *1*, 1562–1565.
- [45] C. A. Antonyraj, J. Jeong, B. Kim, S. Shin, S. Kim, K. Y. Lee, J. K. Cho, *J. Ind. Eng. Chem.* **2013**, *19*, 1056–1059.
- [46] K. Ghosh, R. A. Molla, M. A. Iqbal, S. S. Islam, S. M. Islam, *Appl. Catal. A* **2016**, *520*, 44–52.
- [47] J. Chen, J. Zhong, Y. Guo, L. Chen, *RSC Adv.* **2015**, *5*, 5933–5940.
- [48] Y. Liu, T. Gan, Q. He, H. Zhang, X. He, H. Ji, *Ind. Eng. Chem. Res.* **2020**, *59*, 4333–4337.
- [49] S. Biswas, B. Dutta, A. Mannodi-Kanakkithodi, R. Clarke, W. Song, R. Ramprasad, S. L. Suib, *Chem. Commun.* **2017**, *53*, 11751–11754.
- [50] S. Wen, K. Liu, Y. Tian, Y. Xiang, X. Liu, D. Yin, *Processes* **2020**, *8*, 1–8.
- [51] R. Fang, R. Luque, Y. Li, *Green Chem.* **2016**, *18*, 3152–3157.
- [52] F. Nocito, M. Ventura, M. Aresta, A. Dibenedetto, *ACS Omega* **2018**, *3*, 18724–18729.
- [53] Z. Yuan, B. Liu, P. Zhou, Z. Zhang, Q. Chi, *Catal. Sci. Technol.* **2018**, *8*, 4430–4439.
- [54] Y. Ren, Z. Yuan, K. Lv, J. Sun, Z. Zhang, Q. Chi, *Green Chem.* **2018**, *20*, 4946–4956.
- [55] M. Kim, Y. Su, A. Fukuoka, E. J. M. Hensen, K. Nakajima, *Angew. Chem. Int. Ed.* **2018**, *57*, 8235–8239; *Angew. Chem.* **2018**, *130*, 8367–8371.
- [56] M. Kim, Y. Su, T. Aoshima, A. Fukuoka, E. J. M. Hensen, K. Nakajima, *ACS Catal.* **2019**, *9*, 4277–4285.
- [57] L. Shuai, M. T. Amiri, Y. M. Questell-Santiago, F. Héroguel, Y. Li, H. Kim, R. Meilan, C. Chapple, J. Ralph, J. S. Luterbacher, *Science* **2016**, *354*, 329–333.
- [58] W. Lan, M. T. Amiri, C. M. Hunston, J. S. Luterbacher, *Angew. Chem. Int. Ed.* **2018**, *57*, 1356–1360; *Angew. Chem.* **2018**, *130*, 1370–1374.
- [59] Y. M. Questell-Santiago, R. Zambrano-Varela, M. Talebi Amiri, J. S. Luterbacher, *Nat. Chem.* **2018**, *10*, 1222–1228.
- [60] Y. M. Questell-Santiago, J. H. Yeap, M. Talebi Amiri, B. P. Le Monnier, J. S. Luterbacher, *ACS Sustainable Chem. Eng.* **2020**, *8*, 1709–1714.
- [61] X. Luo, Y. Li, N. K. Gupta, B. Sels, J. Ralph, L. Shuai, *Angew. Chem. Int. Ed.* **2020**, *59*, 11704–11716; *Angew. Chem.* **2020**, *132*, 11800–11812.
- [62] K. Ebitani, K. Motokura, K. Mori, T. Mizugaki, K. Kaneda, *J. Org. Chem.* **2006**, *71*, 5440–5447.
- [63] S. E. Davis, B. N. Zope, R. J. Davis, *Green Chem.* **2012**, *14*, 143–147.
- [64] I. Krivtsov, M. Ilkaeva, E. I. García-López, G. Marci, L. Palmisano, E. Bartashevich, E. Grigoreva, K. Matveeva, E. Díaz, S. Ordóñez, *ChemCatChem* **2019**, *11*, 2713–2724.
- [65] H. F. Ren, X. Luo, K. Zhang, Q. Cai, C. L. Liu, W. S. Dong, *J. Porous Mater.* **2020**, *27*, 1003–1012.

Manuscript received: January 10, 2022
Revised manuscript received: February 11, 2022
Accepted manuscript online: February 11, 2022
Version of record online: February 23, 2022