

## Structural aspects of bismuth molybdate (Bi<sub>2</sub>MoO<sub>6</sub>)

**Citation for published version (APA):**

van den Elzen, A. F., Boon, L., & Metselaar, R. (1983). Structural aspects of bismuth molybdate (Bi<sub>2</sub>MoO<sub>6</sub>). *Studies in Inorganic Chemistry*, 3(Solid Stat), 773-776.

**Document status and date:**

Published: 01/01/1983

**Document Version:**

Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

**Please check the document version of this publication:**

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

**General rights**

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

[www.tue.nl/taverne](http://www.tue.nl/taverne)

**Take down policy**

If you believe that this document breaches copyright please contact us at:

[openaccess@tue.nl](mailto:openaccess@tue.nl)

providing details and we will investigate your claim.

## STRUCTURAL ASPECTS OF $\text{Bi}_2\text{MoO}_6$

A.F. VAN DEN ELZEN, L. BOON and R. METSELAAR

Laboratory of Physical Chemistry, Eindhoven University of Technology,  
P.O. Box 513, 5600 MB Eindhoven (The Netherlands)

### ABSTRACT

The change of the structure of the metastable, catalytic active  $\gamma\text{-Bi}_2\text{MoO}_6$  was followed by x-ray diffraction techniques. The  $\gamma\text{-Bi}_2\text{MoO}_6$  phase transforms via an intermediate phase in the temperature region 400-600°C irreversibly to the  $\gamma'\text{-Bi}_2\text{MoO}_6$  phase. The positions of the metal-ions in this phase were determined.

### INTRODUCTION

According to different authors the compound  $\text{Bi}_2\text{MoO}_6$  is a line compound or has a narrow existence area. Several modifications have been reported in literature (ref. 1,2,3). In this study we have followed both x-ray diffraction patterns and electrical conductivity from room temperature up to the melting point at 938°C.

### STRUCTURE OF THE $\gamma$ -PHASE

The  $\gamma$ -phase (Koechlinite structure) is of special interest because of its catalytic activity in oxidation reactions of alkenes. The space group is  $\text{Pca}2_1$ , with cell dimensions  $a = 5.487$ ,  $b = 16.226$  and  $c = 5.506$  Å (Rhombic symmetry). The structure consists of alternating  $[\text{MoO}_4^{2-}]_N$  and  $[\text{BiO}^+]_{2N}$  layers perpendicular to the b-axis (ref. 4)\*. The  $\gamma$ -phase is metastable and gradually transforms to the catalytic inactive  $\gamma'$ -phase at temperatures above 600°C. An intermediate phase is reported to occur in the temperature region 400-600°C [1]. Cell parameters, as calculated from the positions of six simple and three composed peaks, under which two reflections coincided, are shown as a function of the temperature in Fig. 1. The cell volume increases linearly with the temperature ( $\beta = 6.0 \cdot 10^{-5} \text{ }^\circ\text{C}^{-1}$ ) up to 400°C, as shown in fig. 2. Above this temperature there is a much steeper increase and finally we obtain the  $\gamma'$ -phase.

\* Recent investigations [5] indicate that the structure also can be described with the spacegroup  $\text{Pbca}$ . However the resulting changes in the atomic coordinates do not influence the conclusions of this paper.

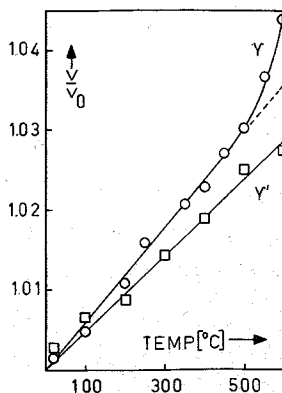
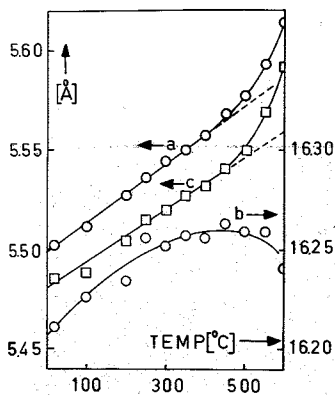


Fig. 1. Cell parameters of the  $\gamma$ -phase as function of the temperature [left].

Fig. 2. Relative cell volume of the  $\gamma$  and  $\gamma'$ -phase as function of temperature [right].

These structural changes are reflected by changes in the electrical conductivity.

#### STRUCTURE OF THE $\gamma'$ -PHASE

The spacegroup is  $P_{21}^2$  with cell dimensions  $a = 17.250$ ,  $b = 22.426$ ,  $c = 5.586$  Å and  $\beta = 90.50^\circ$  (Monoclinic symmetry), as determined by refinement of powder diffraction data. For the indices of the strongest reflections one could recognize the diffraction pattern of a face-centered cell with dimensions  $1/3a^* = 5.75$  Å,  $1/4b^* = 5.61$  Å,  $c^* = 5.59$  Å and  $\beta = 90.50^\circ$ . The elementary cell of  $\gamma'$ - $\text{Bi}_2\text{MoO}_6$  then consists of 12 of such cells. The structure of the  $\gamma'$ - $\text{Bi}_2\text{MoO}_6$  phase can be derived from the fluorite structure by replacing three  $\text{Ca}^{2+}$ -ions by two  $\text{Bi}^{3+}$ -ions and one  $\text{Mo}^{6+}$ -ion; the fluorine ions are replaced by oxygen ions. The dependence of the cell parameters, as calculated from the positions of three simple and two composed peaks, is shown as a function of the temperature in Fig. 2. The cubic dilatation coefficient is  $4.5 \cdot 10^{-5} \text{ } ^\circ\text{C}^{-1}$ . It is impossible to determine the exact positions of the oxygen-ions from the


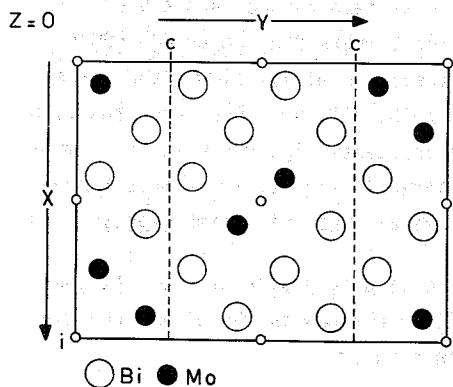


Fig. 3. A cross-section through the elementary cell of  $\gamma'$ - $\text{Bi}_2\text{MoO}_6$ . Only the positions of the metal-ions<sup>6</sup> are shown.

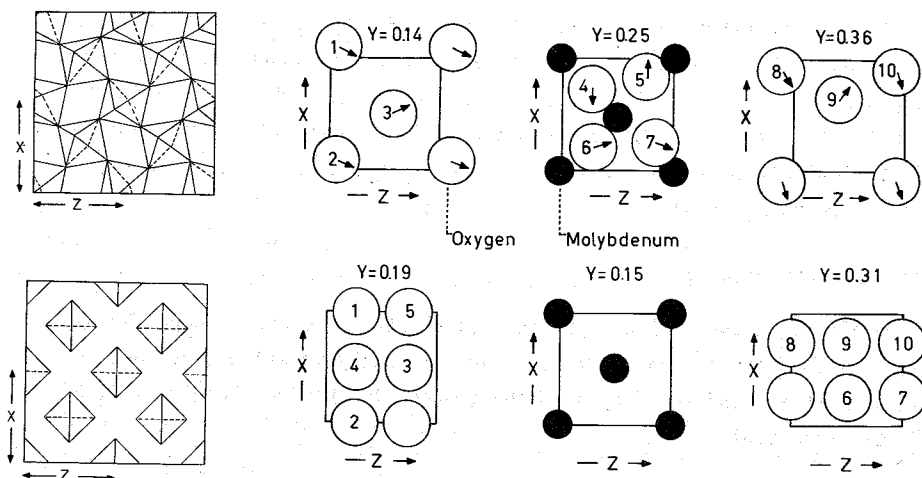

Figs. 4 and 5. [left]  $\text{MoO}_4^{2-}$ -layer perpendicular to the  $b$ -axis of the  $\gamma$ -phase (above).  $\text{MoO}_4^{2-}$ -layer of the  $\gamma''$ -phase (under).  
 Fig. 6. Cross-sections perpendicular to the  $b$ -axis through the  $\text{MoO}_4^{2-}$ -layer of  $\gamma$ -phase (above) and the  $\gamma''$ -phase (below). Arrows in the big circles (oxygen ions) represent the displacement in the  $xz$ -plane. The numbers of the oxygen ions in the different structures correspond [right].

powder diffraction data. A cross section through the elementary cell is given in Fig. 3. The large values of the cell-parameters of the  $a$ - and  $b$ -axis is caused by ordering in the distribution of bismuth and molybdenum-ions over the cation-sublattice.

#### TRANSFORMATION OF THE $\gamma$ TO THE $\gamma''$ -PHASE

Lanthanummolybdate,  $\text{La}_2\text{MoO}_6$ , has like koechlinite a layer structure and is constructed of alternating layers with the compositions  $[\text{LaO}^+]_{2N}$  and  $[\text{MoO}_4^{2-}]_N$ . The  $[\text{LaO}^+]$ -layers are identical with the  $[\text{BiO}^+]$ -layers in koechlinite. The  $[\text{MoO}_4^{2-}]$ -layer in lanthanummolybdate consists of separate  $\text{MoO}_4^{2-}$ -tetrahedrons, whereas the  $\text{MoO}_4^{2-}$ -octahedrons in koechlinite are interconnected at the corners. With increasing temperature the layer with interconnected molybdenum-oxygen-octahedrons gradually transforms into a layer with separate  $\text{MoO}_4^{2-}$ -tetrahedrons as shown in Figs. 4 and 5.

The oxygen ions in the  $(\text{MoO}_4^{2-})$ -layer of the  $\gamma$ -phase only need to be displaced about  $0.9 \text{ \AA}$  in the  $xz$  plane and about  $0.9 \text{ \AA}$  in the  $y$ -direction and the tetragonal  $\text{La}_2\text{MoO}_6$  structure arises. This is illustrated in Fig. 6, in which a number of cross sections perpendicular to the  $b$ -axis through the  $(\text{MoO}_4^{2-})$ -layers is given. The change of cell parameters as a function of the temperature can be explained by the formation of a closed-packed plane of oxygen-ions above and

below the molybdenum plane. Parallel to the b-axis the distance of the oxygen-ions to the molybdenum ions decreases, which explains the temperature dependence of the b-axis. The irreversible transformation to the  $\gamma'$ -phase apparently involves a reordering in the distribution of metal ions over the cationsublattice. This transformation is accomplished in 24 hours at 600°C and in a few hours at 700°C.

#### ELECTRICAL CONDUCTIVITY

As mentioned above, all changes in crystal structure are accompanied by changes in electrical conductivity. We are presently investigating, whether these changes are due to changes in the transportmechanism. Results will be published separately.

#### CONCLUSIONS

The reversible character of the  $\gamma \rightarrow \gamma''$  transition can be understood on the basis of the small changes in the atomic positions of the oxygen ions. The loss of the catalytic activity of  $\text{Bi}_2\text{MoO}_6$  after transformation to the  $\gamma'$ -phase seems to be due to a drastic change in crystal structure, resulting in the loss of the layer structure of the  $\gamma$ -phase.

#### REFERENCES

- 1 L. Erman, E. Gal'perin and B. Sobolev, Russ. J. of Inorg. Chem. 16, (1971) 258-261.
- 2 R. Kohlmüller, J.P. Badaud, Bull. Soc. Chim. France 10, (1969), 3434-3439.
- 3 M. Egashira, K. Matsuo, S. Kagawana and T. Seiyama, J. Catal. 58, (1979), 409-418.
- 4 A.F. van den Elzen and G.D. Rieck, Acta Cryst. B29, (1973), 2436-2438.
- 5 F. Pertlik and J. Zemann, to be published in "Fortschritte der Mineralogie", 1982.