

# Evaluation of experimental techniques for the determination of the shear strength of composite materials

***Citation for published version (APA):***

Govaert, L. E., Kok, de, J. M. M., & Peijs, A. A. J. M. (1991). Evaluation of experimental techniques for the determination of the shear strength of composite materials. In I. Verpoest, & F. R. Jones (Eds.), *Interfacial phenomena in composite materials '91 : proceedings of the second international conference, held 17-19 September 1991 in Leuven, Belgium* (pp. 263-264). Butterworth-Heinemann.

***Document status and date:***

Published: 01/01/1991

***Document Version:***

Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

***Please check the document version of this publication:***

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

***General rights***

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

[www.tue.nl/taverne](http://www.tue.nl/taverne)

***Take down policy***

If you believe that this document breaches copyright please contact us at:

[openaccess@tue.nl](mailto:openaccess@tue.nl)

providing details and we will investigate your claim.

# EVALUATION OF EXPERIMENTAL TECHNIQUES FOR THE DETERMINATION OF THE SHEAR STRENGTH OF COMPOSITE MATERIALS

L.E. Govaert, J.M.M. de Kok and A.A.J.M. Peijs

Centre for Polymers and Composites, Eindhoven University of Technology  
P.O.Box 513, 5600 MB Eindhoven, The Netherlands

In this study three well-known experimental techniques for the determination of the shear strength of composite materials are evaluated: a) fibre pull-out, b) Interlaminar Shear Strength (ILSS) and c) torsion of pultruded rods. It is shown that the applied loading in the fibre pull-out and ILSS-test is far from pure shear, resulting in experimental values that deviate markedly from the actual shear strength. However, experimental data of various epoxy based composite materials reveal a linear relationship between the ILSS values and the quantitative shear strengths as obtained in torsion.

Keywords: Composite Materials, Interfacial Shear Strength, Experimental Techniques

## INTRODUCTION

The level of adhesion between a reinforcing fibre and the surrounding matrix has a strong influence on the performance of composite materials with respect to failure mode, fatigue and energy absorption upon impact loadings. Consequently, optimization of the level of adhesion between fibre and matrix is still subject of considerable research.

A characteristic parameter to evaluate the level of adhesion on the fibre-matrix interface is the interfacial shear strength. For the experimental determination of this parameter a great variety of test methods is available. Unfortunately, however, the experimental values of the shear strength, as obtained by various techniques, usually do not compare. An obvious reason for this discrepancy seems to be the inability of several methods to create a pure shear stress situation in the sample. The variety in the resulting 3-dimensional stress situation will inherently affect the failure of the interface, and consequently the obtained value of the shear strength.

To illustrate the influence of a 3-dimensional loading situation on the experimental values of the shear strength, three well-known experimental techniques were evaluated: a) fibre pull-out, b) interlaminar shear strength (ILSS) and c) torsion of pultruded rods.

## 3-DIMENSIONAL STRESS SITUATION

The complexity of the loading situation in an ILSS test was already pointed out by Berg et al. [1]. By means of Finite Element Method (F.E.M.) analysis the presence of considerable compressive stresses was demonstrated.

F.E.M. -analysis of a fibre pull-out test (Fig.1) indicates that the applied loading condition is also far from a pure shear situation, displaying a considerable tensile stresses in radial, tangential and axial direction.

In both cases the deviation of a pure shear loading situation will inevitably influence the obtained value of the interfacial shear strength. As the 3-D loading situation is not identical for both techniques, the obtained values of the shear strength by fibre pull-out and ILSS will inherently not compare.

### RELATION TO ACTUAL SHEAR STRENGTH

The discrepancy between the ILSS-test and fibre pull-out has been experimentally verified by Elkink et al. [2]. However, although the experimental values of both methods differ, they are linearly related.

To evaluate the qualitative value of the shear strengths obtained by ILSS, the ILSS values of several epoxy based composite materials were compared with shear strengths obtained in a pure shear geometry, being torsion on pultruded rods.

Although ILSS in general supplies a higher value for the shear strength compared to those obtained in torsion, it is shown in Fig. 2 that both values are linearly related. This linear relation indicates that the ILSS method can very well be used for a qualitative evaluation of the shear strength.

### References

1. Berg C.A., Tirosh J., Israeli M. Composite Materials: Testing and Design 2nd Conference ASTM STP 497 (1972) 206-218
2. Elkink, F. in: Integration of fundamental Polymer Science and Technology Part 3 Elsevier Appl. Sci. Publ. (1989) 228-234

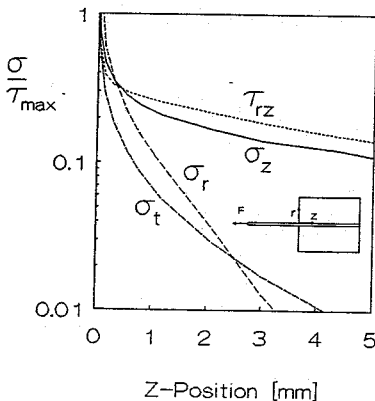


Figure 1. Normal- and shear stresses along the fibre-matrix interface in a fibre pull-out loading geometry

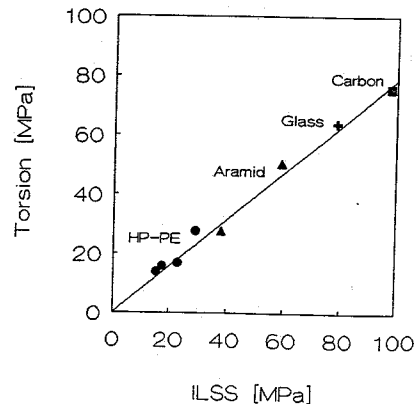


Figure 2. Torsional Shear Strength vs Interlaminar Shear Strength (ILSS) for various epoxy based composite materials