

Indirect determination of trabecular bone effective tissue properties using micro-finite element simulations

Citation for published version (APA):

Verhulp, E., Rietbergen, van, B., Müller, R., & Huiskes, H. W. J. (2005). *Indirect determination of trabecular bone effective tissue properties using micro-finite element simulations*. Poster session presented at Mate Poster Award 2005 : 10th Annual Poster Contest.

Document status and date:

Published: 01/01/2005

Document Version:

Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

Please check the document version of this publication:

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

www.tue.nl/taverne

Take down policy

If you believe that this document breaches copyright please contact us at:

openaccess@tue.nl

providing details and we will investigate your claim.

Indirect determination of trabecular bone effective tissue properties using micro-finite element simulations

E. Verhulp¹, B. van Rietbergen¹, R. Müller² and R. Huiskes¹

¹Eindhoven University of Technology, Department of Biomedical Engineering

²Swiss Federal Institute of Technology (ETH) and University of Zurich, Institute for Biomedical Engineering

Introduction

Osteoporotic fractures mainly occur at sites with relatively large amounts of trabecular bone. The devastating effects of such fractures can be prevented with accurate predictions of trabecular bone strength. Micro-finite element (μ FE) models have been successfully used to study and predict trabecular bone elastic and yield properties. Strength predictions, on the other hand, require the post-yield behavior of trabecular bone tissue. Due to experimental difficulties this data is not available. The purposes of this study were to (1) indirectly determine the tissue properties using μ FE models by iteratively fitting of simulation to experimental results for a trabecular bone specimen and (2) test to what extent the post-yield behavior of other similar specimens can be predicted when using these parameters in μ FE analyses.

Materials and methods

Seven cylindrical trabecular bone specimens were obtained from bovine tibiae. The samples were compressed in a micro-compression device [1] to create high-resolution CT scans of their original and deformed state. At the same time, the load-displacement curve was measured. The scans of the original structures were converted to μ FE models. Following Cezayirlioglu [2], the element were divided into two groups depending on their loading mode (tension or compression) as a result of a linear analysis.

A single specimen with median volume fraction (sample 0) was chosen for the fit procedure. First, the properties of the trabecular tissue were based on cortical bone. The yield and post-yield properties were subsequently adjusted in order to get the same apparent load-displacement curve. The resulting properties were used to simulate the compression of the remaining bone samples. The load-displacement curves and local deformations in the scans were used to validate the μ FE analyses.

Results

The results showed that the apparent behavior of the selected trabecular bone specimen could be accurately simulated with the μ FE model when the tissue properties

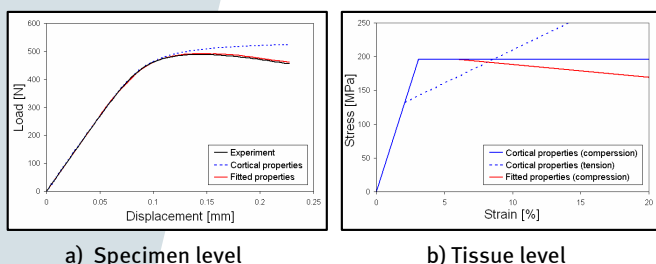


Fig. 1: μ FE-model results before and after the fit procedure compared with the apparent behavior of sample 0 (a), and the accompanying stress-strain relations for the tissue (b).

were adjusted (Fig. 1). The resulting properties were similar to those of cortical bone, but ‘compression softening’ had to be introduced to obtain the typical descent in the load-displacement curve seen during compression tests. The fitted tissue behavior for sample 0 was used to simulate the compression experiments of the remain six samples. The results are shown in Fig. 2.

Validation on a local level revealed extreme deformations and localized high strains in the μ FE meshes (Fig. 3). Cracks were also observed at those locations.

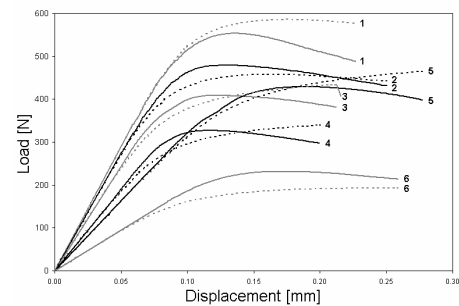


Fig. 2: Apparent load-displacement curves of samples 1 – 6. The experimental data is represented with solid lines. The dotted lines are obtained with μ FE models that incorporate the tissue properties from the fit procedure.

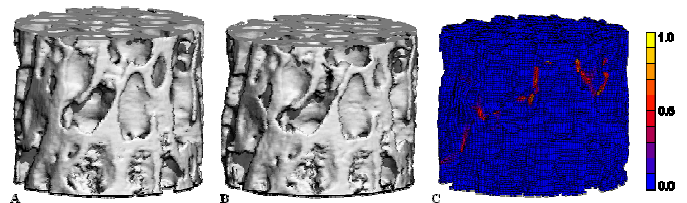


Fig. 3: Rendered CT scans of sample 0 in its initial (A) and deformed (B) state. The deformed μ FE mesh (C) is shown for comparison. Local deformations in the CT scans compared well with deformations and high equivalent strain values in the μ FE models.

Conclusions

The fit procedure resulted in an accurate reproduction of the measured load-displacement curve of the selected specimen. However, the force-displacement curves of the other specimens predicted from μ FE analyses based on the fitted tissue parameters compared less favourable to the experimental data. Natural variations exist in bone tissue properties [3]. It is not clear whether the differences in Fig. 2 are caused by this variations or by other factors, such as experimental artifacts or the formation of cracks, which are not accounted for in the μ FE analyses.

References:

- [1] MÜLLER ET AL., Techn Health Care 6:433-444, 1985.
- [2] CEZAYIRLIOGLU ET AL., J Biomech 18:61-69, 1985.
- [3] GUO, In: Bone Mechanics Handbook, CRC Press, 2001.