

Atomic layer deposition of LiCoO₂ thin film electrodes for all-solid-state Li-ion micro-batteries

Citation for published version (APA):

Donders, M. E., ArnoldBik, W. M., Knoops, H. C. M., Kessels, W. M. M., & Notten, P. H. L. (2013). Atomic layer deposition of LiCoO₂ thin film electrodes for all-solid-state Li-ion micro-batteries. *Journal of the Electrochemical Society*, 160(5), A3066-A3071. <https://doi.org/10.1149/2.011305jes>

DOI:

[10.1149/2.011305jes](https://doi.org/10.1149/2.011305jes)

Document status and date:

Published: 01/01/2013

Document Version:

Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

Please check the document version of this publication:

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

www.tue.nl/taverne

Take down policy

If you believe that this document breaches copyright please contact us at:

openaccess@tue.nl

providing details and we will investigate your claim.



Atomic Layer Deposition of LiCoO₂ Thin-Film Electrodes for All-Solid-State Li-Ion Micro-Batteries

M. E. Donders,^{a,b} W. M. Arnoldbik,^c H. C. M. Knoop,^b W. M. M. Kessels,^{b,*}
and P. H. L. Notten^{b,*,z}

^aMaterials innovation institute M2i, 2600 GA Delft, The Netherlands

^bEindhoven University of Technology, 5600 MB Eindhoven, The Netherlands

^cAccTec B.V., Eindhoven University of Technology, 5600 MB Eindhoven, The Netherlands

One of the remaining challenges in the field of portable electronics is the miniaturization of lithium-ion batteries. To prepare all-solid-state batteries with a sufficient high storage capacity it is vital to prepare high quality thin films for battery stacks on 3D-structured substrates. A remote plasma atomic layer deposition (ALD) process has therefore been developed for LiCoO₂ which can serve as a cathode material. A combination of CoCp₂ as cobalt precursor, Li^oBu as lithium precursor and O₂ plasma as oxidant source was used to create super-cycles to deposit LiCoO₂ from Co₃O₄ and Li₂CO₃ cycles. The thin films were deposited at a temperature of 325°C and showed linear growth with a rate of 0.06 nm/cycle. After annealing the samples at 700°C for 6 minutes high temperature phase LiCoO₂ was obtained, as was demonstrated by XRD and Raman spectroscopy. A new procedure was proposed to obtain the composition of all three chemical elements in the LiCoO₂ films. Elastic Backscattering Spectroscopy (EBS) measurements turned out to be very convenient and reliable to obtain the quantities of all chemical elements, including lithium. Moreover, the ALD-deposited LiCoO₂ thin film electrodes were electrochemically characterized, revealing good electrochemical performance. To the best of our knowledge this paper provides the first evidence that electrochemically active LiCoO₂ can be deposited by ALD.

© 2013 The Electrochemical Society. [DOI: 10.1149/2.011305jes] All rights reserved.

Manuscript submitted December 31, 2012; revised manuscript received February 21, 2013. Published March 12, 2013. This was in part Paper 1848 presented at the Boston, Massachusetts, Meeting of the Society, October 9–14, 2011. *This paper is part of the JES Focus Issue on Intercalation Compounds for Rechargeable Batteries.*

During the past decade, portable electronic devices have become considerably more widespread, complex and powerful, and new challenges have been encountered, especially in the field of medical and autonomous devices. To power these future devices, thin-film, all-solid-state, lithium-ion micro-batteries have been proposed.^{1–4} To facilitate the required energy demand, both a high energy-to-weight and energy-to-volume ratio is essential. Lithium-ion batteries fulfill these demands. As packaging requirements become more dominant at smaller dimensions, one of the remaining challenges is miniaturization of lithium-ion batteries without decreasing the storage capacity. This formed the basis of the integrated batteries concept.¹

Step conformal deposition of films onto etched structures in silicon is an excellent method to tackle this challenge and to facilitate the integration of these high capacity energy storage devices into micro-electronics.^{1,2} Chemical vapor deposition (CVD) has been proposed as deposition method.¹ However, CVD has a limited step-conformal deposition capability in highly structured geometries due to the delicate interplay between kinetics and diffusion. By using atomic layer deposition (ALD) this effect can be counteracted as this deposition method is based on a reaction-limited surface saturation, opening up numerous possibilities for the use of more complex substrate structures such as nanowires.⁵

Industrial scale implementation of ALD has already been proven in micro-electronics and this technique is rapidly penetrating new fields, such as solar cells, catalysis and recently also energy storage devices.^{1,6,7} In the field of battery technology several interesting materials have been prepared which show much promise.⁸ However, work on lithium-containing solid-state electrolytes and electrode materials is still very exploratory. Even though several lithium-containing compounds have recently been prepared by ALD,^{9,10} no reports of electrochemical investigations are available to date. An overview of Li-containing compounds prepared by ALD is presented in Table I. This paper demonstrates the electrochemical activity for ALD-prepared LiCoO₂ which is, to the best of our knowledge, the first active Li-containing battery material, deposited by ALD, which is electrochemically characterized in detail. Therefore, for reference, also LiCoO₂ CVD processes are included in Table I.

Evidently, analyzing the chemical composition of thin films is essential to evaluate the electrochemical properties of the LiCoO₂. Although it is most uncommon to use backscattering techniques such as Rutherford backscattering spectroscopy (RBS) for the determination of the Li content in thin films, this has been achieved by making use of non-Rutherford cross sections. The as-obtained results will be verified by Nuclear Reaction Analyzes (NRA).¹¹ This is another novelty within this paper.

Experimental

Film preparation.— The LiCoO₂ films were deposited using an open-load thermal and remote plasma ALD reactor as described previously for the deposition of Co₃O₄.¹² An inductively coupled plasma (ICP) source that is operated on O₂ is connected to a deposition chamber along with a pump unit through gate valves. The pump unit consists of a rotary and turbo molecular pump, which can reach a base pressure of <10⁻⁵ Torr by overnight pumping. The CoCp₂ and Li^oBu precursors (both 98%, Strem Chemicals) were heated to 80°C and 120°C respectively (Table II) and they were bubbled with Ar at a reactor pressure of 0.02 Torr. The substrate was heated to 325°C, while the reactor walls, Ar lines, and CoCp₂ precursor lines were maintained at a temperature of 105°C, the Li^oBu precursor lines were kept at 150°C to prevent precursor condensation. Si(100) with native oxide and Si(100) with 400 nm thermally grown SiO₂ were used as substrates for materials analyzes. For the electrochemical characterization, Si/TiO₂/Pt substrates were prepared by ALD as described in Ref. 8 and schematically shown in Fig. 1⁸ with thicknesses of 5 and 20 nm for TiO₂ and Pt respectively.

The remote plasma ALD process for LiCoO₂ consists of the two individual ALD processes for the deposition of Co₃O₄ and Li₂CO₃ which are combined in a so-called super-cycle (Fig. 2). Here the previously described remote plasma ALD process for Co₃O₄ is combined with a novel ALD process, using a lithium precursor reported recently for the deposition of LLT and Li₂CO₃.^{9,10} In this paper a super-cycle is defined as a combination of *A* cycles Co₃O₄ and *B* cycles Li₂CO₃ (Fig. 2), resulting in a dosing ratio of *A*:*B* (e.g. 4:1), where *B* is consistently kept as 1 throughout the paper. *x* is defined as *A*/*B*, e.g. for a dosing ratio of 4:1, *x* equals 4. In both processes a precursor dosing time of 2 s is applied combined with an O₂ plasma at 100 W for 5 s

*Electrochemical Society Active Member.

^zE-mail: P.H.L.Notten@tue.nl

Table I. Overview of ALD processes for the deposition of lithium-containing compounds and CVD processes for LiCoO₂. The growth rates have not been reported for the CVD processes. The abbreviation LLT stands for lithium lanthanum titanate.

	Deposited material	Lithium precursor	Other Precursor(s)	Reactant(s)	Deposition temperature	Growth rate	References
ALD	Li ₂ CO ₃	LiO ^t Bu	—	H ₂ O	225°C	0.08 nm/cycle	9, 10
	LLT	LiO ^t Bu	La(thd) ₃	O ₃	225°C	0.05 nm/cycle	10
	LiOH	LiO ^t Bu	—	H ₂ O	225°C	0.09 nm/cycle	9
	LiCoO ₂	LiO ^t Bu	CoCp ₂	O ₂ plasma	325°C	0.06 nm/cycle	This work
CVD	LiCoO ₂	^t BuLi	CpCo(CO) ₂	O ₂	300–600°C	—	19
	LiCoO ₂	Li(TMHD)	Co(TMHD) ₃	O ₂ / N ₂	450–550°C	—	17

Table II. Overview of ALD process parameters for the Co₃O₄ and Li₂CO₃ sub-cycles used in the super-cycle for the preparation of LiCoO₂.

	Precursor/reactant	Dosing time	Pump purge time	Precursor temperature	Precursor line temperature
Co ₃ O ₄	CoCp ₂	2 s	3 s	80°C	105°C
	O ₂ plasma	5 s	0.5 s	—	—
Li ₂ CO ₃	LiO ^t Bu	2 s	3 s	120°C	150°C
	O ₂ plasma	5 s	0.5 s	—	—

at a pressure of 0.01 Torr. During and after the precursor dosing and plasma exposure, the reaction chamber is purged (3 s and 0.5 s respectively) and evacuated.


Film analyzes.— The thickness and dielectric function of the films were monitored during the ALD process by in situ spectroscopic ellipsometry (SE) with a J.A. Woollam, Inc. M2000U (0.75–5.0 eV) ellipsometer.¹³ The optical range was extended to 6.5 eV after the deposition process, using ex situ variable angle measurements with a J.A. Woollam, Inc. M2000D ellipsometer. The dielectric function of Co₃O₄ has been extracted from the SE measurements using an optical model employing a Gauss, a Tauc–Lorentz, and two Lorentz oscillators, to account for the absorption bands.¹² The dielectric functions of Li₂CO₃ and LiCoO₂ were parameterized using a mathematical description in the form of B-splines.¹⁴ This is a method that requires no prior knowledge about the dielectric function of deposited films and enables in situ thickness measurements.

The microstructure of the LiCoO₂ films was studied using Grazing Incidence X-ray diffraction (GI-XRD) with a Philips X'Pert MPD diffractometer equipped with a Cu K_α source (1.54 Å radiation). The Raman spectra of the samples were recorded using a (in-via Renishaw) micro Raman scattering setup with a wavelength of 514.5 nm, a maximum power density of 3.2 · 10⁵ W/cm² and a resolution of 1.6 cm⁻¹.

The overall composition of the layers has been analyzed at AccTec BV¹⁵ with backscattering spectrometry using a 2.09 MeV proton beam delivered and a scattering angle of 172°. Under these circumstances the cross sections of the lighter elements are strongly enhanced with respect to the Rutherford cross sections and strictly spoken the technique should be referred to as Elastic Backscattering (EBS) instead of RBS. The enhancement for the cross sections of ⁷Li, ¹²C, ¹⁶O with respect to the Rutherford values is about 55, 5 and 4 respectively. The main advantage is that all elements can now be determined from one single spectrum. The alpha yield was simultaneously measured from the ⁷Li(p,α)⁴He nuclear reaction to confirm the Li content with NRA. The Co, O and C concentrations have been confirmed with conventional RBS measurements using 2 MeV He⁺ ions. More details of the EBS analysis will be published in a separate paper.¹¹

Electrochemical analyzes.— The electrochemical analyzes were performed in three-electrode cylindrical electrochemical cells with an effective surface area of 2 cm² (Fig. 1). The cells were made of Teflon with a volume of about 15 ml. The cells were assembled in an argon-filled glove-box. The Si/TiO₂/Pt/LiCoO₂ electrodes were mounted as working electrodes and back-contacted, and in direct contact with LiCoO₂, with silver paint to facilitate good electrical conductivity. A

Cu plate was used as electrical conductor for the working electrode, while pure lithium foils were used as counter and reference electrodes. 1 molar LiClO₄ dissolved in Ethyl Carbonate (EC)/Diethyl Carbonate (DEC) was used as liquid electrolyte (Puriel, Techno, Semiche Co., Ltd, Korea). The cells were placed in a stainless steel holder that was thermostatically controlled at room temperature. Contaminants in the glove-box (water and oxygen) were monitored and controlled below 1 ppm. Galvanostatic cycling was performed with a M2300 galvanostat (Maccor, Tulsa, USA), applying a current density of 0.5 μAh/cm² between 3.0 and 4.1 V. The following definition is adopted throughout the manuscript: charging LiCoO₂ refers to Li-ion extraction (or delithiation) and discharging to Li-ion insertion (or lithiation). Based on the electrode surface area, the layer thickness as determined by spectroscopic ellipsometry and the density determined by quantitative EBS measurements (Table III), the volumetric and gravimetric capacities were calculated.

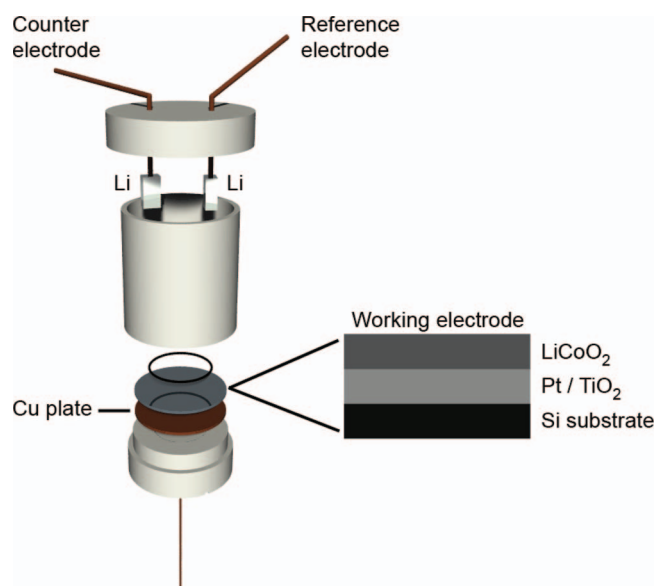**Figure 1.** Schematic representation of the Teflon three-electrode measurement setup. The LiCoO₂ films under investigation deposited on Si/TiO₂/Pt substrates are used as working electrode during the electrochemical measurements. Layer thicknesses are 5 and 20 nm for TiO₂ and Pt respectively.

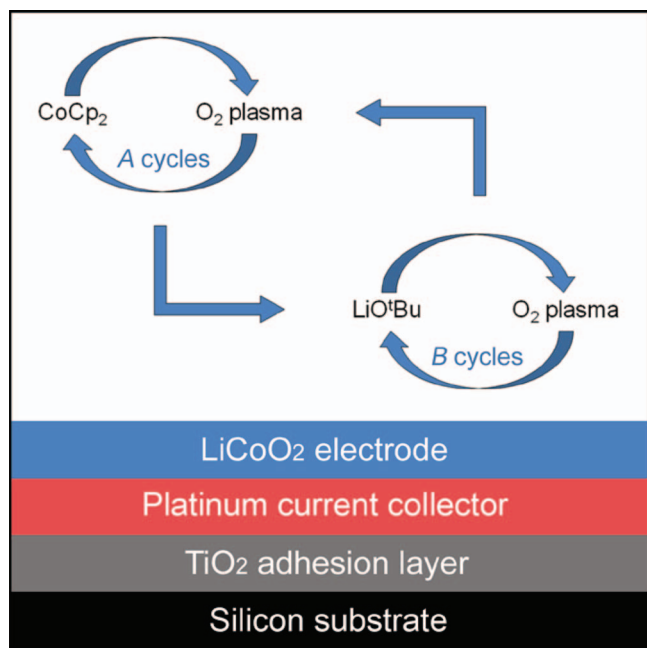


Figure 2. Schematic representation of an ALD super-cycle consisting of the two individual ALD processes for Co_3O_4 and Li_2CO_3 . A cycles of the Co_3O_4 process are combined with B cycles of the Li_2CO_3 process. The film-substrate stack is also shown.

Results and Discussion

ALD growth.— To investigate the ALD process parameters, the self-limiting behavior of the ALD process was investigated for the CoCp_2 and LiOtBu precursors using a Co:Li dosing ratio of 1:1 for the super-cycle as presented in Fig. 2. This means that one cycle of Co_3O_4 was alternated with one cycle of Li_2CO_3 . The plasma exposure time was fixed at 5 seconds for both precursors. The Li precursor dosing time was varied while the Co dosing time remained constant at 2 s, which is the same dosing time used during the deposition of Co_3O_4 .¹² Saturation of the Li precursor occurs after about 2 s as can be seen in Fig. 3a. The same procedure was conducted for the Co precursor while the Li dosing time was kept constant at 2 s. Proper saturation is also observed in the Co case (Fig. 3b). Note that the growth rates under saturated conditions are slightly different in Fig. 3a and 3b. This can most likely be attributed to the different film thicknesses employed when generating Fig. 3a and 3b. the growth rate was found the change

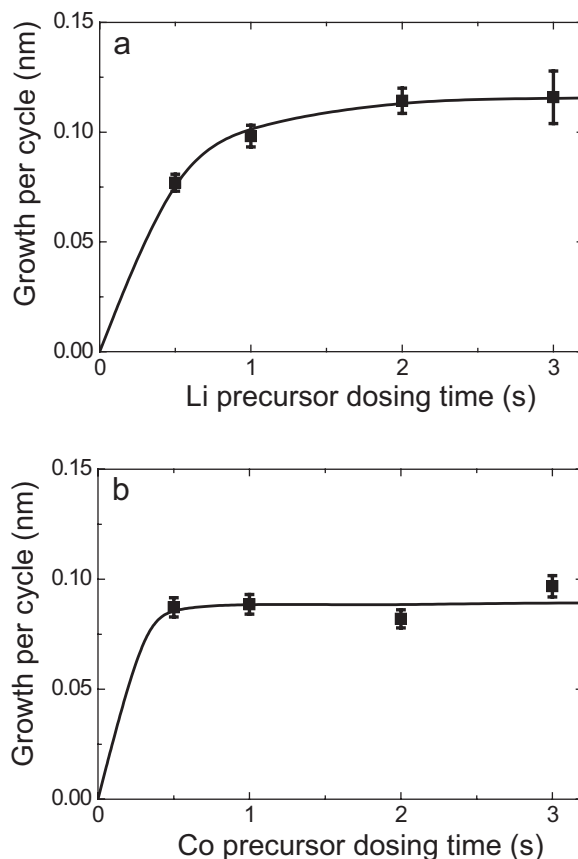


Figure 3. Saturation curves for remote plasma ALD of LiCoO_2 at 325°C (a) Growth rate as a function of LiOtBu dosing time, while the CoCp_2 dosing time and the plasma exposure time are kept constant at 2 s and 5 s respectively. (b) Growth rate as a function of CoCp_2 dosing time, while the LiOtBu dosing time and the plasma exposure time are kept constant at 2 s and 5 s respectively. The lines serve as guides to the eye.

slightly with film thicknesses (see Fig. 4). Dosing times of 2 s for both precursors were therefore fixed for all deposition experiments described.

Applying a Co:Li dosing ratio of 1:1 lead to a slightly higher growth rate than expected on the basis of the individual growth rates for Co_3O_4 (0.05 nm/cycle) and Li_2CO_3 (0.08 nm/cycle). This could be due to the high growth rate of pure Li_2CO_3 as compared to pure Co_3O_4 ,^{9,12} but

Table III. Material properties and electrochemical results for LiCoO_2 thin films prepared for various Co/Li dosing ratios. Compositions are measured by EBS. The Co/Li dosing ratio (x) for the ALD process is defined as the number of Co_3O_4 sub-cycles divided by the number of Li_2CO_3 sub-cycles. For the lithium concentration an average is taken of the EBS and NRA measurements. Typical experimental errors are: Co (3%), Li (5%), O (5%) and C (7%).

	Co/Li dosing ratio (x)	2	3	4	5
ALD process	Super-cycles	300	200	200	169
	Cycles (total)	900	800	1000	1014
	Thickness (nm) (± 0.5 nm)	54	48	60	61
Composition	Co (10^{15} atom/ cm^2)	45.3	51.6	79.0	83.6
	Li (10^{15} atom/ cm^2)	149	98.7	91.6	101
	O (10^{15} atom/ cm^2)	353	210	266	315
	C (10^{15} atom/ cm^2)	86	41	30	37
	Average Co/Li ratio	0.30	0.52	0.86	0.83
	Average O/Co ratio	7.9	4.1	3.5	3.8
	Composition		$\text{Li}_{3.3}\text{CoO}_{7.9}$	$\text{Li}_{1.9}\text{CoO}_{4.1}$	$\text{Li}_{1.2}\text{CoO}_{3.5}$
Electrochemical results	Density ($\text{g} \cdot \text{cm}^{-3}$)	3.2	2.6	2.8	3.0
	Average Capacity ($\mu\text{Ah} \cdot \mu\text{m}^{-1} \cdot \text{cm}^{-2}$)	12.1	–	27.0	–
	Average Capacity (% of maximum)	28	–	62	–

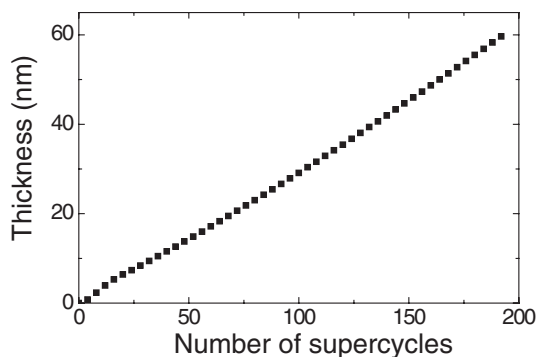


Figure 4. Thickness of LiCoO₂ on Si(100) as a function of the number of ALD super-cycles, as measured with in situ spectroscopic ellipsometry. The used Co:Li dosing ratio is 4:1.

the growth of Li₂CO₃ could also be catalyzed by the presence of cobalt atoms. Fig. 4 shows that the thickness was almost linearly dependent on the number of ALD cycles at a dosing ratio of Co:Li = 4:1 with an overall growth rate of ~0.06 nm/cycle. It is not expected that a change in Co:Li dosing ratio will significantly affect the saturation behavior for both precursors in the Co₃O₄ and Li₂CO₃ cycles.

Fig. 5 shows the in situ measured dielectric function ϵ_2 for photon energies between 1.24 and 6.5 eV of the as-deposited Co₃O₄, Li₂CO₃ and LiCoO₂. A clear difference is found between the three films. The dielectric function of Co₃O₄ has been described in an earlier publication.¹² Unfortunately, from the literature not much is known about the dielectric functions of Li₂CO₃ and LiCoO₂. In order to distinguish between Co₃O₄, Li₂CO₃ and LiCoO₂ the films of the latter two materials have also been investigated. Fig. 5 clearly shows that Li₂CO₃ hardly contributes to the LiCoO₂ signal and that a typical spectrum for LiCoO₂ is obtained.

Material properties.— Knowledge of the overall film composition is essential in order to evaluate ALD-deposited LiCoO₂ thin films, especially to properly evaluate the electrochemical results. EBS and NRA are excellent techniques to determine the atomic composition of compounds and can thus be used to reveal the ratio between lithium, cobalt and oxygen in the films (Fig. 6).¹¹ These analyzes show that materials prepared with a Co:Li dosing ratio x of 4 and higher have more or less the same atomic ratios (Table III). In addition, a Co:Li dosing ratio larger than 4:1 seems to increase the deposition rate of the lithium sub-cycle in the ALD process slightly (Fig. 6), while the deposition rate during the cobalt sub-cycle is unaffected and continues to increase linearly with x . This effect is not yet fully understood, but limits the ALD process from obtaining the desired Co/Li = 1 material composition for the range investigated. This illustrates the delicate balance that needs to be taken into account when dealing with the ALD-deposition of ternary compounds.

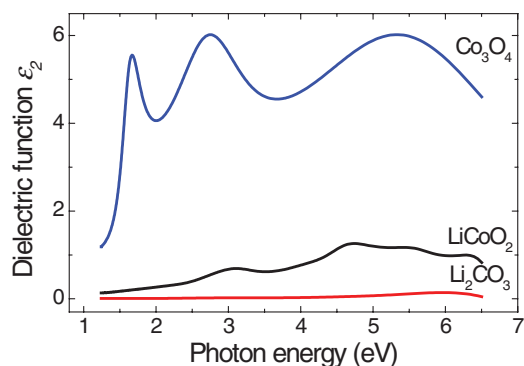


Figure 5. The imaginary part of the dielectric function (ϵ_2) of the Co₃O₄, Li₂CO₃ and LiCoO₂ films as determined by in situ spectroscopic ellipsometry.

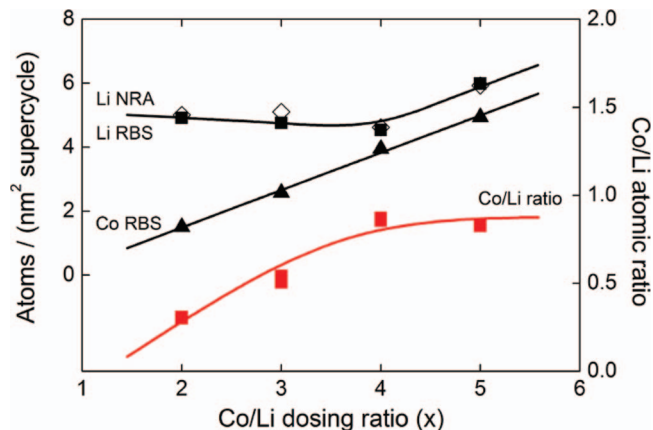


Figure 6. Number of atoms deposited per nm² per super-cycle and the Co/Li ratio in the film as a function of the Co/Li dosing ratio (x) as determined by Nuclear reaction analysis (NRA) and Elastic backscattering spectroscopy (EBS). For the Co/Li dosing ratio the amount of Li cycles per super-cycle is kept constant at 1.

As-deposited samples were investigated by GI-XRD and Raman spectroscopy and subsequently annealed at 700°C for 6 minutes before being measured again with the same techniques. Fig. 7 shows that a large diffraction peak becomes visible after annealing at a 2θ angle of 19°, which has also been reported in the literature for metal organic (MO) CVD deposited LiCoO₂ at various temperatures.¹⁶ This peak can be assigned to either the (111) reflection of Co₃O₄ or the (003) reflection of LiCoO₂. As both cobalt oxide and lithium cobalt oxide can be present in the deposited thin films it is not possible to unambiguously determine the origin of the diffraction peak and the nature of the film from XRD. Therefore Raman spectroscopy has been used to further investigate these films. Figure 8 shows that the high temperature (HT) hexagonal phase of LiCoO₂ is observed with two typical phonon modes at 486 and 596 cm⁻¹ which becomes even more defined after annealing.¹⁷ The Raman spectra reveal no significant fraction of Co₃O₄ in the films as this would lead to a distinct peak at 693 cm⁻¹.

Electrochemical analyzes.— It is well-known that a heat-treatment of about 700°C is required to obtain the electrochemically active, crystalline, LiCoO₂.¹⁸ The annealed LiCoO₂ films were electrochemically characterized in the experimental three-electrode battery set-up using

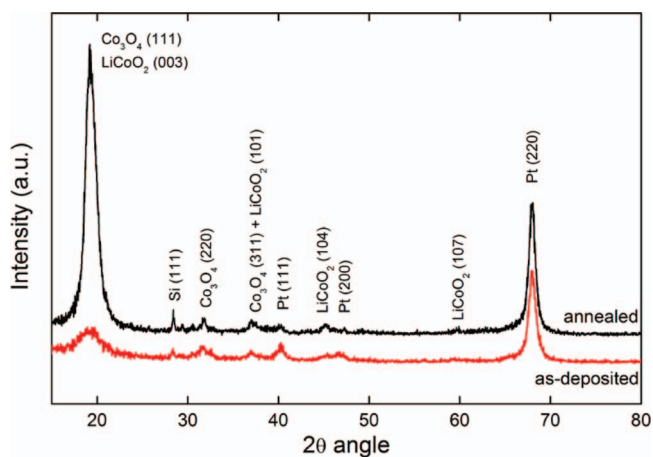


Figure 7. X-ray diffraction measurements ($\lambda = 1.54 \text{ \AA}$) revealing overlapping peaks for Co₃O₄ with a preferential (111) orientation and crystalline LiCoO₂ after annealing at 700°C for 6 minutes. The spectra have been offset vertically for clarity. The Co:Li dosing ratio was 2:1 ($x = 2$).


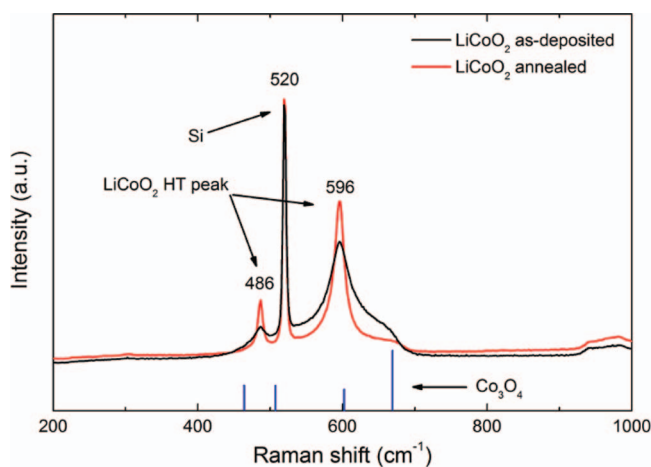


Figure 8. Raman measurements for LiCoO₂ annealed at 700°C for 6 minutes compared to as-deposited LiCoO₂ and the theoretical spectrum of Co₃O₄. The used Co:Li dosing ratio was 2:1 ($x = 2$).

constant current (dis)charge cycling. The charge transfer reaction of the LiCoO₂ electrode can be represented by



where $z \leq 0.5$. Extracting more than 0.5 lithium atoms per formula unit would irreversibly change the crystal structure of LiCoO₂, making the electrode (partly) electrochemically inactive.²⁰ All electrode films investigated showed electrochemical activity. However, the storage capacity was clearly found to be dependent on the ALD dosing ratio.

Fig. 9a shows the (dis)charge behavior of the LiCoO₂ electrode for the Co:Li dosing ratio x of 4 which revealed the highest storage capacity. By taking the derivative of the storage capacity with respect to the electrode potential (Fig. 9b), the plateaus in Fig. 9a are transformed into either broad or sharp peaks dependent on the slope of the voltage curves. A clear charge transfer reaction is now visible at 3.9 V as expected for LiCoO₂.^{18,21} Also a 12% capacity loss between the charge and discharge reactions is found (Fig. 9a). A similar effect has been reported before¹⁹ and this has been attributed to irreversible side reactions (e.g. oxidation of the liquid electrolyte,²² the formation of the less electrochemically active spinel LiCo₂O₄ phase²³ or mechanical strain-induced degradation of the LiCoO₂ film,²⁴ but also the (electro)chemical stability of the impurities found in ALD LiCoO₂ with respect to the liquid electrolyte could play a role.

The electrochemical storage capacity is, however, lower than theoretically expected for LiCoO₂ (155 mAh/g),¹⁸ but remained fairly stable upon cycling as shown in Fig. 9c. Over 60% of the maximum theoretical storage capacity has been obtained with the ALD deposited ($x = 4$) thin film electrode (Fig. 9c). This lower capacity can be explained by the presence of Li₂CO₃ within the thin film as indicated by the increased oxygen over cobalt (O/Co) and decreased cobalt over lithium (Co/Li) ratios and the presence of carbon (Table III). Moreover Table III shows an abundance of lithium and oxygen which could also indicate the formation of inactive Li₂O during the ALD process. These two effects may contribute to the reduced capacity compared to the theoretical maximum. Referring to Table III it is clear that the impurity level of the $x = 2$ material is significantly higher than the $x = 4$ material. This is in line with the reduced capacity of the $x = 2$ material compared to $x = 4$. It is expected that further process optimization will yield a higher chemical purity and improved storage capacity.

Conclusions

A remote plasma ALD process for the preparation of LiCoO₂ thin films was developed using the combination of CoCp₂ as cobalt precursor, LiO^tBu as lithium precursor and a O₂ plasma as the oxidant

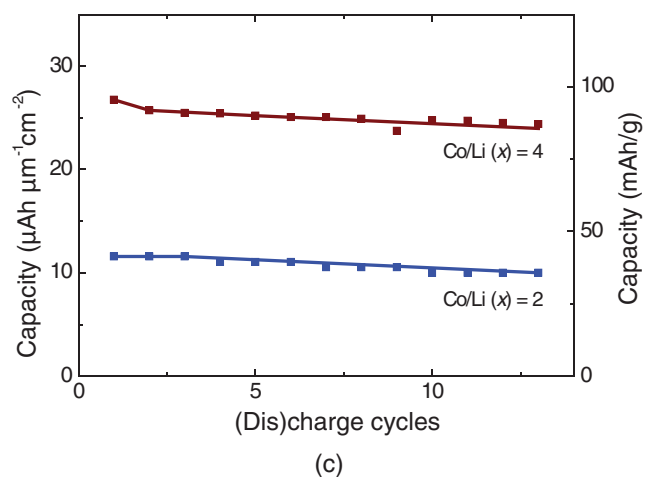
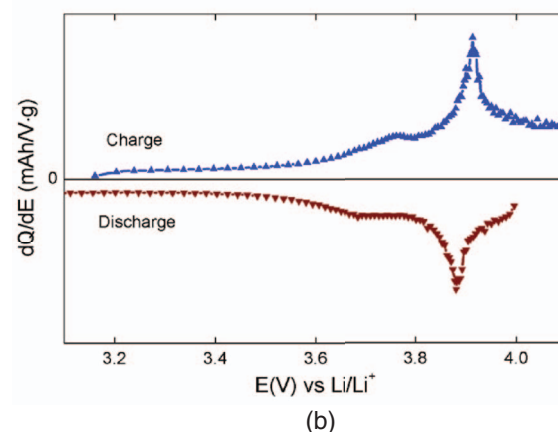
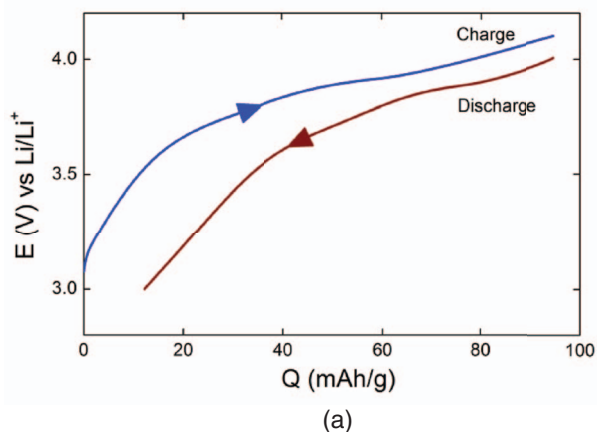


Figure 9. Constant current (CC) (dis)charge cycling between 3.0 V and 4.1 V (0.35 C-rate) for an ALD-deposited LiCoO₂ ($x = 4$) film on Si/TiO₂/Pt, using LiClO₄ in ethylene carbonate/diethyl carbonate (EC/DEC 1/1) as liquid electrolyte. (a) (dis)charge of LiCoO₂, (b) the derivative of the storage capacity with respect to the electrode potential and (c) the electrochemical storage capacity upon cycling showing data for $x = 2$ and $x = 4$.

source. To the best of our knowledge this paper provides the first evidence that electrochemically active LiCoO₂ can be deposited by ALD. It was shown that LiCoO₂ films could be deposited by ALD with the Li/Co ratio depending on the Co:Li dosing ratio. Moreover elastic backscattering spectrometry was shown to be an accurate method to analyze the Li-content in this type of films, which simplifies the analysis significantly. After heat-treatment the high temperature phase of LiCoO₂ was obtained as shown by XRD and Raman measurements.

Electrochemical charge/discharge cycling experiments showed good reversible electrochemical performance with a significant fraction (60%) of active material for the annealed LiCoO₂ films, revealing that ALD is a promising method to deposit active lithium-containing electrode materials.

Acknowledgments

This research was carried out under the project number MC3.06278 in the framework of the Research Program of the Materials innovation institute M2i (www.m2i.nl).

References

1. P. H. L. Notten, F. Roozeboom, R. A. H. Niessen, and L. Baggetto, *Adv. Mater.*, **19**, 4564 (2007).
2. M. Armand and J.-M. Tarascon, *Nature*, **451**, 652 (2008).
3. J. W. Long, B. Dunn, D. R. Rolison, and H. S. White, *Chem. Rev.*, **104**, 4463 (2004).
4. M. Roberts, P. Johns, J. Owen, D. Brandell, K. Edstrom, G. El. Enany, C. Guery, D. Golodnitsky, M. Lacey, C. Lecoeur, H. Mazor, E. Peled, E. Perre, M. M. Shaijumon, P. Simon, and P.-L. Taberna, *J. Mater. Chem.*, **21**, 9876 (2011).
5. S. K. Cheah, E. Perre, M. Rooth, M. Fondell, A. Harsta, L. Nyholm, M. Boman, J. Lu, P. Simon, and K. Edstrom, *Nano Lett.*, **9**, 3230 (2009).
6. H. B. Profijt, S. E. Potts, M. C. M. van de Sanden, and W. M. M. Kessels, *J. Vac. Sci. Technol. A*, **29**, 050801 (2011).
7. W. M. M. Kessels and M. Putkonen, *MRS Bulletin*, **36**, 907 (2011).
8. H. C. M. Knoop, M. E. Donders, L. Baggetto, M. C. M. van de Sanden, P. H. L. Notten, and W. M. M. Kessels, *J. Vac. Sci. Technol. A*, **30**, 010801 (2012).
9. A. S. Cavanagh, Y. Lee, B. Yoon, and S. M. George, *ECS Trans.*, **33**, 223 (2010).
10. T. Aaltonen, M. Alnes, O. Nilsen, L. Costelle, and H. Fjellvåg, *J. Mater. Chem.*, **20**, 2877 (2010).
11. M. E. Donders, W. M. Arnoldbik, W. M. M. Kessels, and P. H. L. Notten, *to be published*.
12. M. E. Donders, H. C. M. Knoop, M. C. M. van de Sanden, W. M. M. Kessels, and P. H. L. Notten, *J. Electrochem. Soc.*, **158**, G92 (2011).
13. E. Langereis, S. B. S. Heil, H. C. M. Knoop, W. Keuning, M. C. M. van de Sanden, and W. M. M. Kessels, *J. Phys. D: Appl. Phys.*, **42**, 073001 (2009).
14. J. W. Weber, T. A. R. Hansen, M. C. M. van de Sanden, and R. Engeln, *J. Appl. Phys.*, **106**, 123503 (2009).
15. <http://www.acctec.nl/iba/>.
16. S.-I. Cho and S.-G. Yoon, *J. Electrochem. Soc.*, **149**, A1584 (2002).
17. W.-G. Choi and S.-G. Yoon, *J. Vac. Sci. Technol. A*, **22**, 2356 (2004).
18. J. F. M. Oudenhoven, L. Baggetto, and P. H. L. Notten, *Adv. Energy Mater.*, **1**, 10 (2011).
19. J. F. M. Oudenhoven, T. van Dongen, R. A. H. Niessen, M. H. J. M. de Croon, and P. H. L. Notten, *J. Electrochem. Soc.*, **156**, D169 (2009).
20. D. Danilov and P. H. L. Notten, *5th IEEE Vehicle Power and Propulsion Conference*, pp. 5289835-320 (2009).
21. H. Porthault, F. Le Cras, and S. Franger, *J. Power Sources*, **195**, 6262 (2010).
22. K. Kanamura, *J. Power Sources*, **81-82**, 123 (1999).
23. H. Gabrisch, R. Yazami, and B. Fultz, *J. Power Sources*, **119-121**, 674 (2003).
24. H. Wang, Y.-I. Jang, B. Huang, D. R. Sadoway, and Y. M. Chiang, *J. Electrochem. Soc.*, **146**, 473 (1999).