

Predicting deformation and failure of plastics

Citation for published version (APA):

Janssen, R. P. M., Govaert, L. E., & Meijer, H. E. H. (2005). *Predicting deformation and failure of plastics*. Poster session presented at Mate Poster Award 2005 : 10th Annual Poster Contest, .

Document status and date:

Published: 01/01/2005

Document Version:

Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

Please check the document version of this publication:

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

www.tue.nl/taverne

Take down policy

If you believe that this document breaches copyright please contact us at:

openaccess@tue.nl

providing details and we will investigate your claim.

Predicting Deformation and Failure of Plastics

R.P.M. Janssen, L.E. Govaert, H.E.H. Meijer

Eindhoven University of Technology, Department of Mechanical Engineering

Introduction

Constitutive modeling can be used to design plastic products without the need of costly experiments. An in-house developed model [1] is recently modified to describe thermo-rheological complex behavior [2]. This study explores its performance using amorphous polystyrene (PS) and polymethylmethacrylate (PMMA) and semi-crystalline polypropylene (PP).




Figure 1 An example: numerical life-time predictions can reduce costs in the design of plastic gaspipes.

Theoretical Background

In thermo-rheological simple materials (PC above roomtemperature) only the primary glass-transition (α) is present, whereas for thermo-rheological complex materials (PMMA) also a secondary glass-transition (β) is present, see figure 2a. The β -process typically causes strain rate dependent yield stress and yield drop behavior as displayed in figure 2b. Therefore, the model is modified in a way described elsewhere [2].

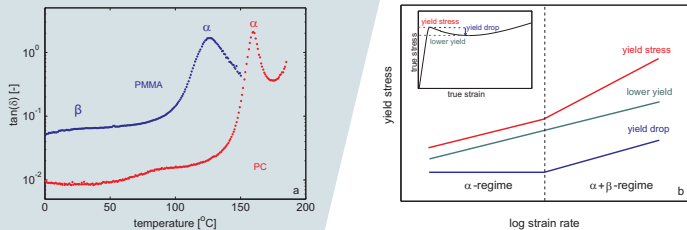


Figure 2 a) Glass-transitions in PC and PMMA. b) Strain rate dependence of yield behavior.

Materials and Methods

Figure 3 shows how the parameter set is obtained. First compression tests on PMMA, PS and PP are performed at various strain rates. For validation, tensile and creep tests are performed on tensile bars of two grades of PMMA with a different thermal history. However, only one parameter S_a is changed and is determined by a tensile test, see reference point in figure 4a.

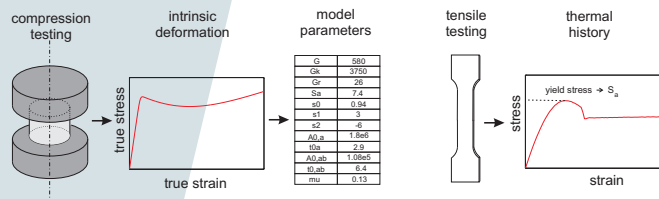


Figure 3 Characterization of intrinsic deformation behavior.

Characterization of Intrinsic Deformation

Figure 4a shows the experimental intrinsic deformation (symbols) and its numerical description (lines). The blue curves exhibit α -behavior, but also the β -process is captured, as the black curves show. Moreover, figure 4b shows that the yield stress is described in both regions. The modified model also captures the intrinsic deformation of PS and PP, see figures 4c and 4d.

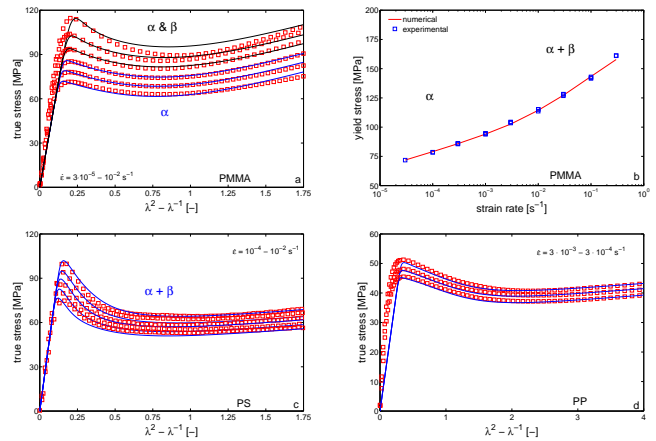


Figure 4 The model captures a) PMMA, α and β , b) PMMA, yield stress, c) PS, α and β -region, d) semi-crystalline PP.

Validation: Predictions for PMMA

Figure 5 shows that the model predicts (lines) accurately the tensile yield stress and creep life-time (symbols) of two PMMA-grades based on the S_a determined at the reference point using the same parameter set.

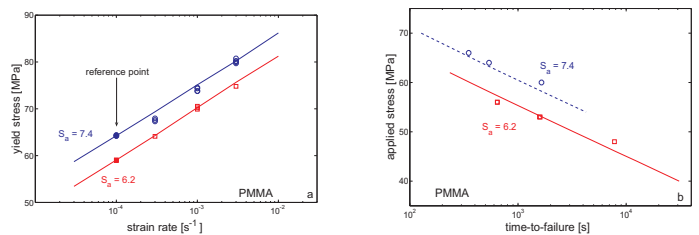


Figure 5 Predictions for PMMA of a) the tensile yield stress, b) the creep life-time.

Conclusions

- The modified model successfully describes thermo-rheological complex deformation behavior.
- The model predicts yield and failure behavior of multiple PMMA-grades using the same parameter set.

References:

[1] E.T.J. KLOMPEN, PHD-THESIS, 2005
 [2] L.C.A. VAN BREEMEN ET AL., MATE POSTER CONTEST 2005