

## Modeling flow-induced crystallization of polymers

***Citation for published version (APA):***

Steenbakkens, R. J. A., Peters, G. W. M., & Meijer, H. E. H. (2005). *Modeling flow-induced crystallization of polymers*. Poster session presented at Mate Poster Award 2005 : 10th Annual Poster Contest.

***Document status and date:***

Published: 01/01/2005

***Document Version:***

Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

***Please check the document version of this publication:***

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

***General rights***

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

[www.tue.nl/taverne](http://www.tue.nl/taverne)

***Take down policy***

If you believe that this document breaches copyright please contact us at:

[openaccess@tue.nl](mailto:openaccess@tue.nl)

providing details and we will investigate your claim.

# Modeling Flow-Induced Crystallization of Polymers

R.J.A. Steenbakkers, G.W.M. Peters and H.E.H. Meijer

## Introduction

A framework for modeling flow-induced crystallization of polymers is being developed. The effect of crystallites on the rheology of the melt is accounted for by a suspension model. The flow-induced crystallization kinetics are described by a model for the creation and growth of (unstable) precursors and their transformation into (stable) nuclei.

## Modeling

### Suspension rheology

In the linear viscoelastic regime the dynamic modulus is written as

$$G^* = f_G^*(\xi_g, G_0^*, G_1^*, \dots) G_0^*. \quad (1)$$

We use the generalized self-consistent method (GSCM [1]) to calculate the relative dynamic modulus  $f_G^*$  from the space filling index  $\xi_g$ . The results are compared to a widely used scaling law,

$$G' = [G'_1 - G'_0] \xi_g + G'_0, \quad (2)$$

for the storage modulus. An extension to nonlinear viscoelastic behavior is currently being made.

### Flow-induced crystallization kinetics

The rate of change of the number of precursors is given by the evolution equation

$$\dot{N}_p = I_p + \dot{T} \frac{\partial N_{pa}}{\partial T} - \frac{N_p}{\tau_{pd}} - \frac{N_p}{\tau_{pn}} \quad (3)$$

with the nucleation rate

$$\dot{N}_n = \frac{N_p}{\tau_{pn}}. \quad (4)$$

The rheology of the melt is described by the eXtended Pom-Pom (XPP) model. We use a modified Zuidema model [2] for the rate of sporadic creation of precursors,

$$I_p = \tilde{g}_p (\Lambda^4 - 1), \quad (5)$$

where  $\Lambda = \sqrt{\text{tr}(\mathbf{B}_e)/3}$  is the backbone stretch of the highest relaxation mode. The ‘branching’ parameter  $q$  of the XPP model is related to the number of flow-induced precursors as

$$q = q_0 [1 + a N_{pf}]. \quad (6)$$

A depletion of molecules long enough to form precursors [3] is incorporated in  $\tilde{g}_p$ . Furthermore, we assume that flow inhibits nucleation. A simple step function, where  $\tau_{pn}$  jumps from infinity to zero as the flow is switched off, suffices for the experiments used here. Growth of pointlike precursors into threadlike precursors is also modeled, but this part has not been validated by experiments yet.

## Validation

In figure 1 the storage modulus, calculated from the experimentally determined  $\xi_g$ ,  $G_0^*$  and  $G_1^*$ , is compared to the storage modulus measured after short-term shearing of a linear isotactic polypropylene (iPP) melt at 135°C.

/department of mechanical engineering

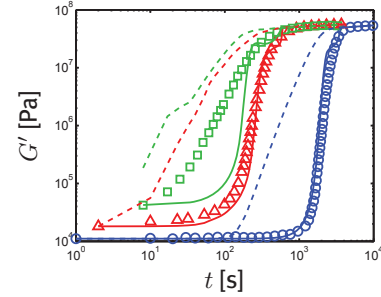


Figure 1. Evolution of the storage modulus after shearing at  $\dot{\gamma} = 60\text{s}^{-1}$  for  $t_s = 0\text{s}$  ( $\circ$ ),  $3\text{s}$  ( $\Delta$ ), and  $6\text{s}$  ( $\square$ ), simulated by the linear scaling law (dashed lines) and the GSCM (solid lines).

Whereas the linear scaling law fails, the GSCM yields good results, except for high shear times (probably due to development of a network structure).

Space filling and nucleation density are predicted quantitatively by the kinetics model for processes where point nucleation dominates, as shown in figure 2 for iPP at 135°C.

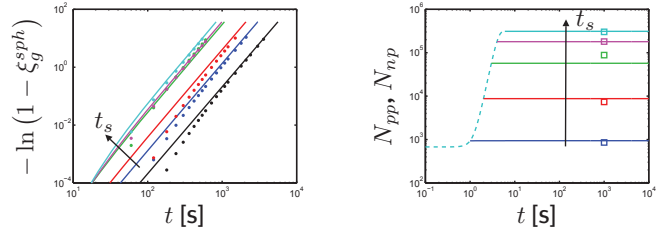


Figure 2. Left: ‘Avrami plot’ of space filling due to spherulites. Right: numbers of pointlike precursors (dashed lines) and nuclei (solid lines). Symbols are data for  $\dot{\gamma} = 60\text{s}^{-1}$  and different  $t_s$ .

An additional validation is provided by the narrow size distribution of crystallites observed in the experiments, which is captured here due to the assumption that precursors are not nucleated until the flow is switched off.

## Conclusions

- Crystallizing polymer melts can be modeled as suspensions. The properties of the phases change due to the evolving microstructure.
- Flow-induced point nucleation is described quantitatively by our model of flow-induced crystallization kinetics.

## Future work

- Describe the transition to oriented growth.
- Simulate crystallization during continuous flow.

## References:

- [1] CHRISTENSEN, R.M. (J. Mech. Phys. Solids 38, 379–404, 1990)
- [2] ZUIDEMA, H.; PETERS, G.W.M.; MEIJER, H.E.H. (Macromol. Theory Simul. 10, 447–460, 2001)
- [3] SOMANI, R.H.; HSIAO, B.S.; NOGALES, A.; SRINIVAS, S.; TSOU, A.H.; SICS, I.; BALTA-CALLEJA, F.J.; EZQUERRA, T.A. (Macromolecules 33, 9385–9394, 2000)