

Measuring the dependency between chemical and mechanical behavior of ionized porous media

Citation for published version (APA):

Roos, R. W., Huyghe, J. M. R. J., & Baaijens, F. P. T. (2002). *Measuring the dependency between chemical and mechanical behavior of ionized porous media*. Poster session presented at Mate Poster Award 2002 : 7th Annual Poster Contest.

Document status and date:

Published: 01/01/2002

Document Version:

Publisher's PDF, also known as Version of Record (includes final page, issue and volume numbers)

Please check the document version of this publication:

- A submitted manuscript is the version of the article upon submission and before peer-review. There can be important differences between the submitted version and the official published version of record. People interested in the research are advised to contact the author for the final version of the publication, or visit the DOI to the publisher's website.
- The final author version and the galley proof are versions of the publication after peer review.
- The final published version features the final layout of the paper including the volume, issue and page numbers.

[Link to publication](#)

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal.

If the publication is distributed under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license above, please follow below link for the End User Agreement:

www.tue.nl/taverne

Take down policy

If you believe that this document breaches copyright please contact us at:

openaccess@tue.nl

providing details and we will investigate your claim.

Measuring the dependency between chemical and mechanical behavior of ionized porous media.

R.W. Roos, J.M. Huyghe, F.P.T. Baaijens

Eindhoven University of Technology, Department of Biomedical Engineering

Introduction

Cartilage is a material with high water content and surprisingly high mechanical strength. It is an example of a porous ionized material. It can be described as a mixture of proteoglycan supra-molecules with a water solution, enmeshed in a resilient collagen network. An odd property of cartilage is its strong swelling propensity due to Donnan osmosis. The resulting prestress in the collagen network contributes to the shear stiffness.

Free energy function

The effective stress in a material is the derivative $\frac{\delta W}{\delta \epsilon}$ of the free energy function W to the strain (ϵ). This function depends on concentration- and a strain. On cartilage, Grodzinsky [1] measured under constant volume that shear stiffness depends on salt concentration. This implies that mixed terms in concentration and strain appear in the free energy:

$$W = W(c^+, c^-) + W(\epsilon) + W(c^+, c^-, \epsilon) \quad (1)$$

This extra term is either caused by the sensitivity of the collagen network to its osmotic environment, or to Maxwell stresses around the proteoglycan chains. In this study we want to discriminate the contribution of these two sources.

Objectives

- Quantify the extra term in an ionized porous medium without collagen: synthetic hydrogel.

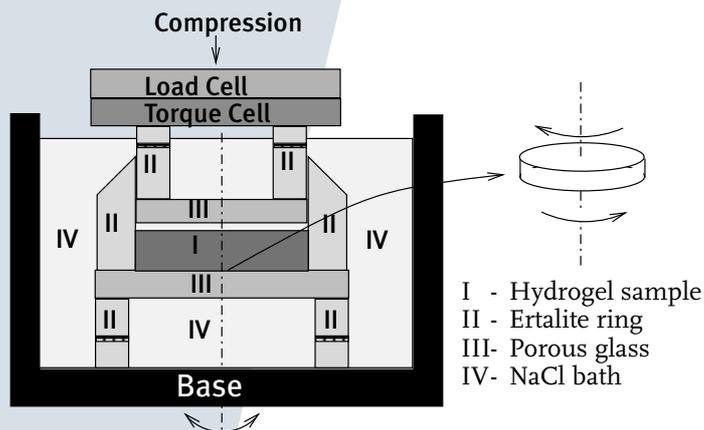


Figure 1 A hydrogel disc is placed in the center of the Plexiglas base chamber filled with NaCl solution at constant temperature. The plastic ring and the porous glass plates prevent the disc from swelling. While the torque cell of the draw-torsion bench (MTS) applies a torque on the disc, the vertical relative angular displacement and the axial force are measured.

Experiment

A cylindrical hydrogel disc is put inside a plastic ring, between two porous glass plates (Fig. 1), fixed between a draw-torsion bench. The sample is in equilibrium with a salt solution. For different salt concentrations of the liquid, the torque-rotation relationship is compared.

Results

Although swelling was not completely prevented, initial results of the experiments are plotted in Figure 2. This graph shows that the shear stiffness varies significantly with the external salt concentration.

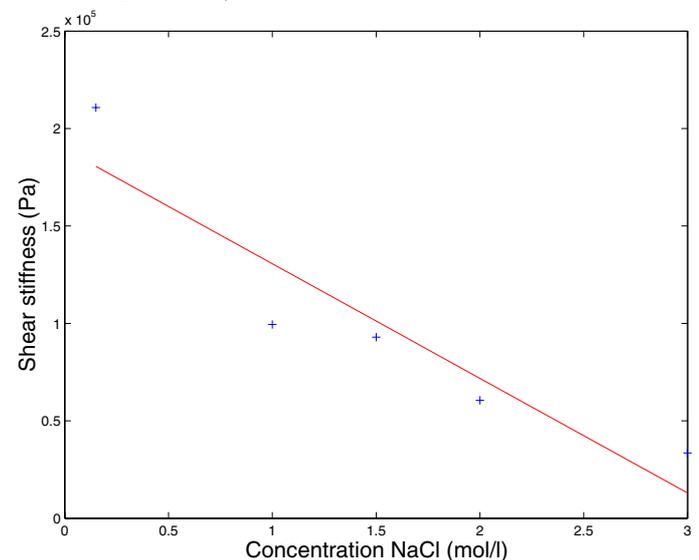


Figure 2 At constant volume, the shear modulus of hydrogel decreases with increasing external salt concentration.

Discussion

The results suggest that hydrogel displays chemical-mechanical interaction, indicating that Maxwell stresses might be an important source of chemical-mechanical interaction in cartilage under shear.

Acknowledgement

This research is supported by the technology foundation STW, applied science division of NWO, and the technology programs of the Ministry of Economics.

References:

- J. Moonsoo and A.J. Grodzinsky: Effect of Electrostatic Interactions between Glycosaminoglycans on the Shear Stiffness of Cartilage: A Molecular Model and Experiments. *Macromolecules*, 2001, 34, 8330-8339.